



A transition-metal-free hydrogenation catalyst: Pore-confined sodium alanate for the hydrogenation of alkynes and alkenes



Peter L. Bramwell^a, Jinbao Gao^a, Bernd de Waal^a, Krijn P. de Jong^a, Robertus J.M. Klein Gebbink^b, Petra E. de Jongh^{a,*}

^aInorganic Chemistry and Catalysis, Debye Institute for Nanomaterials Science, Utrecht University, Universiteitsweg 99, 3583CG, The Netherlands

^bOrganic Chemistry and Catalysis, Debye Institute for Nanomaterials Science, Utrecht University, Universiteitsweg 99, 3583CG, The Netherlands

ARTICLE INFO

Article history:

Received 20 June 2016

Revised 25 August 2016

Accepted 19 September 2016

Available online 6 October 2016

Keywords:

Hydrogenation

Heterogeneous catalysis

Alkene

Alkyne

Sodium alanate

ABSTRACT

Hydrogenation catalysis is dominated by transition metals, but interest in alternative catalysts has been growing over recent years. Herein, a transition-metal-free catalyst is discussed consisting of carbon supported NaAlH₄ as a selective catalyst for hydrogenation. This is illustrated using a range of substrates, and in more detail for the case of diphenylacetylene. Catalytic activity depends on the solvent utilized; in cyclohexane the activity is 2.3 mol (DPA) mol⁻¹ (NaAlH₄) h⁻¹ at 100 bar H₂, 150 °C with a slight preference for the formation of *trans*-stilbene. The catalyst selectivity is influenced by the loading, yielding a high selectivity toward the thermodynamically less stable *cis*-stilbene at low catalyst loadings. This proof of principle shows promise for using metal hydrides based on earth-abundant elements as effective hydrogenation catalysts.

© 2016 Elsevier Inc. All rights reserved.

1. Introduction

Hydrogenation of C–C multiple bonds is a key step in the synthesis of many important compounds [1–3]. As with many other fields of catalysis, transition metals dominate. For example, Pd is widely employed in hydrogenation of alkynes to alkenes [4–8], particularly in the case of the famous Lindlar catalyst [9]. Pd-based catalysts generally show very high activity (turnover frequencies, TOF, of 2500 h⁻¹ at 22 °C) [10] under mild conditions but often relatively low selectivities [11,12].

In recent years a new family of transition-metal-free catalysts, frustrated Lewis pairs, has emerged which boast reasonably high activities (TOFs of 5–40 h⁻¹ at 80 °C) [13] and selectivities toward *cis*-alkenes without utilizing transition metals [14,15]. Light metal hydrides such as LiAlH₄ and NaBH₄ are based on earth-abundant elements and are typically used in the stoichiometric reduction of polar groups such as carbonyls [16,17]. However, these materials so far have seldom been applied to the reduction of alkenes or alkynes and in such cases only as stoichiometric reagents, rather

than as catalysts. There is one isolated example of NaAlH₄ being utilized as a hydrogenation catalyst where Ti and NaAlH₄ were milled together and tested in the hydrogenation of diphenylacetylene [18]. At 130 °C and 100 bar of hydrogen pressure the alkyne starting material was fully hydrogenated to the saturated product within three hours. Ti-doped sodium alanate is known to reversibly store and release hydrogen, which might explain its catalytic activity.

The preparation and characterization of confined light metal hydrides for the purpose of reversible uptake and release of hydrogen (hydrogen storage) at reasonably low temperatures with fast kinetics have been demonstrated in recent years [19–27]. Melt infiltration under hydrogen pressure (to prevent decomposition) can be utilized to prepare these materials. The metal hydride and support are mixed together and heated to the melting point of the hydride. The molten hydride infiltrates the pores and, upon cooling, produces solid metal hydride confined within the pores, which is referred to as nanoconfinement. The resulting material consists of a carbon matrix of which the pores are filled with metal hydride. This pore-confined metal hydride lacks long range crystallinity and demonstrates orders of magnitude faster kinetics of absorption and desorption compared to the corresponding macrocrystalline metal hydride material.

In the case of NaAlH₄ almost full reversibility of hydrogen release and uptake was achieved at 150 °C [21]. Reduction of the

Abbreviations: XRD, X-ray diffraction; SEM, scanning electron microscopy; EDX, energy dispersive X-ray spectroscopy; TPD, temperature programmed desorption; TCD, thermal conductivity detector; DPA, diphenylacetylene; PEG, polyethylene glycol; GC, gas chromatography.

* Corresponding author.

E-mail address: P.E.dejongh@uu.nl (P.E. de Jongh).

particle size improves the kinetics of hydrogen sorption as bulk crystalline NaAlH_4 displays much slower uptake kinetics and requires temperatures above 180°C to desorb hydrogen. Additionally, the presence of carbon alters the hydrogen release profile from a three-step pathway to a two-step pathway, bypassing the intermediate Na_3AlH_6 phase altogether [21]. Nanoconfinement promotes reversibility by preventing the macroscopic phase separation of NaH and Al . All of these factors allow the NaAlH_4/C nanocomposite to release and reabsorb hydrogen in a reversible manner at relatively low temperatures. This raises the interesting question of whether this material could also be used as a hydrogenation catalyst in the absence of any transition metals [18,28]. Hence we demonstrate carbon-confined NaAlH_4 , previously developed for hydrogen storage purposes, as a transition-metal-free hydrogenation catalyst. We explore the hydrogenation of alkynes and alkenes, while studying in detail the recyclability, selectivity, and activity depending on solvent and catalyst loading in the case of DPA hydrogenation (Scheme 1).

2. Experimental section

All materials were stored in a nitrogen-filled glove box (Mbraun Labmaster I30, 1 ppm H_2O , <1 ppm O_2) prior to use, except for the catalyst which was stored in an argon-filled glove box (Mbraun Labmaster dp, 1 ppm H_2O , <1 ppm O_2) and transferred to the other glove box immediately before use. NaAlH_4 powder (hydrogen storage grade), DPA (98%), cyclohexane (anhydrous, 99.5%), dodecane (anhydrous, $\geq 99\%$), 1-octyne (97%), 4-octyne (99%) and styrene (99%) were all obtained from Sigma-Aldrich. Toluene was dried in a distillation apparatus before storage. All liquid reagents and solvents were stored in the glove box over molecular sieves following degassing by bubbling nitrogen gas through the liquid for several hours. DPA was dried *in vacuo* overnight before storage in the glove box. The carbon aerogel was prepared by the sol-gel resorcinol procedure [26] and was analyzed by nitrogen physisorption (performed at -196°C , Micromeritics TriStar) to determine the pore characteristics (BET surface area $564\text{ m}^2\text{ g}^{-1}$, pore volume $0.57\text{ cm}^3\text{ g}^{-1}$, broad pore size distribution with a maximum around 18–20 nm). The aerogel was dried at 600°C under argon flow for 12 h before storing in the argon-filled glove box.


The catalyst was prepared by melt infiltration according to previously reported literature [21] with a loading of 20 wt% NaAlH_4 . The result was analyzed by X-ray Diffraction (Bruker AXS D8 advance 120 machine, Co-K_α radiation, air-tight sample holder used), Temperature Programmed Desorption (Micromeritics AutoChem II, equipped with a TCD detector, Ar flow of 25 mL min^{-1})

and nitrogen physisorption before use in catalytic tests. Multiple batches of the catalyst were prepared using the above procedure and their full characterization can be found in Section S1 of the supporting information.

All hydrogenation reactions were carried out in a Parr 300 mL autoclave at 150°C , 100 bar hydrogen pressure and constant stirring. The autoclave was loaded in the nitrogen glove box. 270 mg of catalyst (1 mmol NaAlH_4) and 890 mg of DPA (5 mmol) were added to 180 mL of solvent. Dodecane was added as an internal standard. Aliquots of reaction mixture were taken for analysis at regular intervals using a sampling arm which was flushed with a small amount of reaction mixture before the taking of each sample (roughly 2 mL of reaction mixture per sample). Samples were then analyzed by Gas Chromatography (GC-2010 Shimadzu gas chromatograph equipped with a Shimadzu AOC-20i Auto injector) using a CP-Wax column to separate the reaction mixture by boiling points; Boiling points: DPA (300°C), *cis*-stilbene (307°C), *trans*-stilbene (305°C), bibenzyl (284°C).

The following blank and reference measurements were performed, the results of which can be found in Sections S2–S3 in the supporting information. The influence of the carbon support on the activity was tested by performing the above catalysis experiments using only 215 mg of the carbon support in the absence of NaAlH_4 . To rule out the effect of the metals in the autoclave walls catalytic tests were performed using a Teflon lining in the autoclave. As the Teflon liner reduced the volume of the reaction vessel the reaction was scaled down by 15%. The catalytic tests were repeated to demonstrate reproducibility. The recyclability of the catalyst was tested by recovering the catalyst at the end of the hydrogenation reaction and re-using in another test. Since 150 mg of the NaAlH_4/C catalyst was recovered (due to losses through filtering and removing the catalyst from the reactor) the catalytic loading in the second reaction was 150 mg instead of 270 mg. Isomerization studies were carried out by performing the reaction in the same manner as above but instead of adding DPA either *trans*-stilbene or *cis*-stilbene was added.

For the experiments on the adsorption of each substrate on the catalyst in different solvents the following procedure was applied. All experiments were performed at room temperature to ensure no hydrogenation reaction occurred. In each experiment a substrate, either DPA, *cis*-stilbene, *trans*-stilbene or bibenzyl, was dissolved in 9 mL of the solvent and stirred for 5 min. This was then analyzed by gas chromatography to determine the substrate concentration at 100%. Then 100 mg of catalyst was added (with a volumetric liquid:solid ratio of 203) to the solution and a sample was taken at 60 min for gas chromatography (GC) analysis. The decrease in

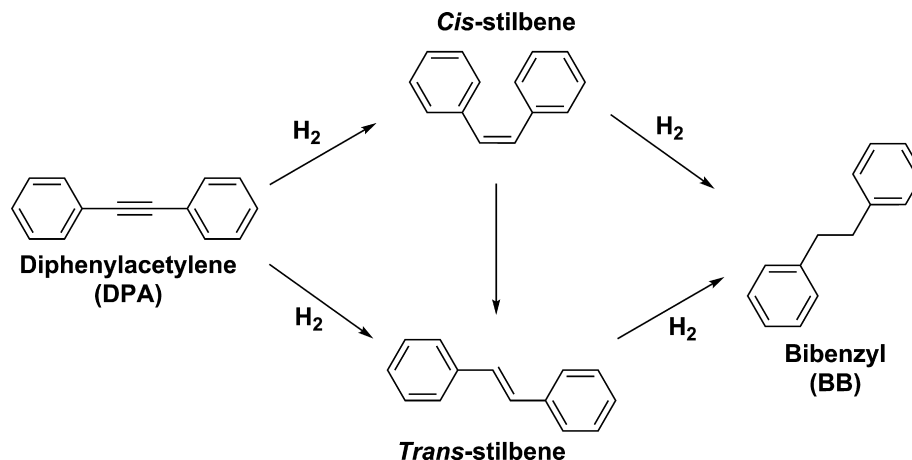

Scheme 1. Reaction scheme showing the hydrogenation of diphenylacetylene to bibenzyl.

concentration was assumed to be due to substrate adsorption on the catalyst surface, allowing the calculation of the quantity of adsorbed substrate. Each sample was run in the GC three times and an average was taken, yielding the points shown in Fig. S6.1, and the variation in these three measurements was then used to calculate the error given in Table 2.

3. Results and discussion

3.1. Catalyst characterization

The catalyst is prepared by melt infiltration of NaAlH₄ into the pore structure of a carbon aerogel support (volume average pore diameter of 13 nm, prepared by the sol-gel resorcinol method) [29]. A schematic of the melt infiltration procedure is shown in Fig. 1. Following melt infiltration X-ray diffraction (XRD) shows the loss of crystalline NaAlH₄ and a small amount of crystalline Al is present. Al is present due to decomposition of a minor fraction of the NaAlH₄ to NaH and Al during melt infiltration [21]. The low intensity of the NaAlH₄ signal shows that pore-confined NaAlH₄ lacks long range crystallinity, where the proportion of crystalline NaAlH₄ is 29% compared to the physical mixture, indicating a confinement of 71% of the NaAlH₄. This is supported by the pore volume loss upon melt infiltration of 26 vol% (± 2 vol%), which accounts for 91% of the NaAlH₄ present. Mapping of the distribution of NaAlH₄ and Al through the catalyst surface has been well studied previously through use of scanning electron microscopy (SEM) and energy dispersive X-ray spectroscopy (EDX) [21]. As a result it is known that the NaAlH₄ is distributed in a homogeneous manner. Hence the catalyst does not contain discrete NaAlH₄ particles but rather the pores are either completely filled or empty, with NaAlH₄ exposed at the pore mouths at the external surface of the carbon support particle, and at the boundaries between filled and unfilled pore regions.

Characterization of the hydrogen content of nanoconfined hydride materials is commonly performed using temperature programmed desorption (TPD) and the temperature at which the hydrogen can be released is also relevant to hydrogenation catalysis. In the NaAlH₄/C nanocomposite hydrogen release (Fig. 2) begins at 100 °C with a maximum release rate at 175 °C and a total emission of 0.37 wt% of hydrogen (compared to a theoretical capacity of 1.48 wt%). This hydrogen release should be reversible

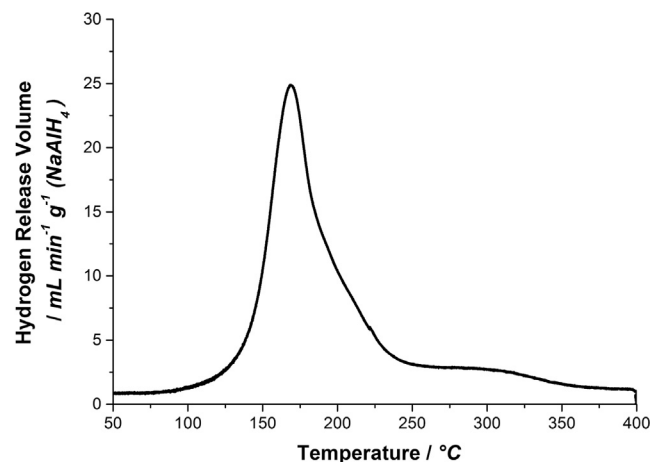


Fig. 2. Temperature programmed desorption profile showing the hydrogen release of the NaAlH₄/C catalyst performed at a heating rate of 5 °C min⁻¹ under 25 mL min⁻¹ Ar flow.

in order for NaAlH₄ to perform hydrogenation reactions in a catalytic manner and full reversibility at 150 °C has indeed been demonstrated in the literature [20], where the optimal reversible hydrogen capacity is achieved with rehydrogenation at 100 bar of H₂. Therefore a temperature of 150 °C was used for all catalytic testing.

3.2. Catalyst testing

Fig. 3 shows the hydrogenation of DPA performed using the NaAlH₄/C catalyst under 100 bar H₂ of pressure. It is clear that the nanocomposite exhibits catalytic behavior by fully hydrogenating DPA when used in a 5:1 DPA:NaAlH₄ molar ratio (turnover number 10) with a molar activity, taken between 90% and 50% DPA conversion, of 2.29 mol (DPA) mol⁻¹ (NaAlH₄) h⁻¹. Due to the nature of the catalyst it is difficult to estimate a turnover frequency (TOF) as it is not possible to measure the amount of exposed active surface area. Only a small amount of the NaAlH₄ in the catalyst is active, as it is confined within the pores; therefore, for this catalyst a large fraction of the NaAlH₄ is not exposed to the reactants. For this reason a TOF range has been calculated with a

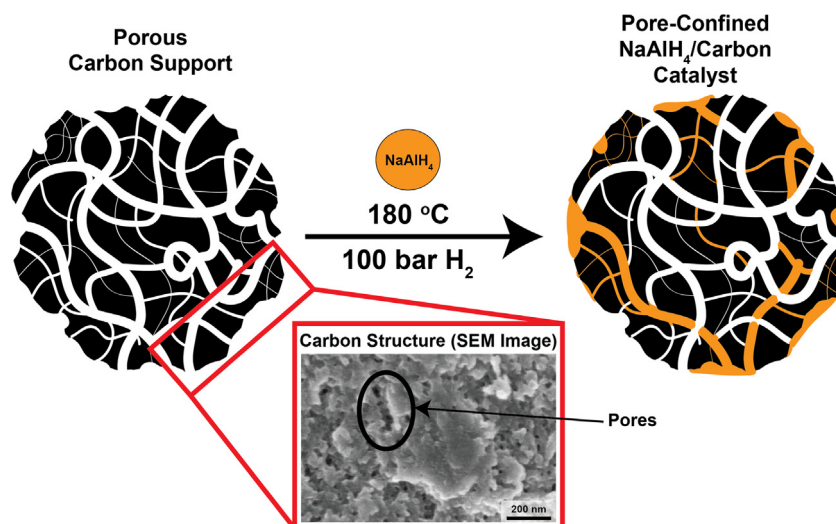


Fig. 1. Schematic representation of the melt infiltration process used in preparing the NaAlH₄ nanocomposite. Orange shading on the right picture represents how the pores are filled by NaAlH₄. (For interpretation of the references to color in this figure legend, the reader is referred to the web version of this article.)

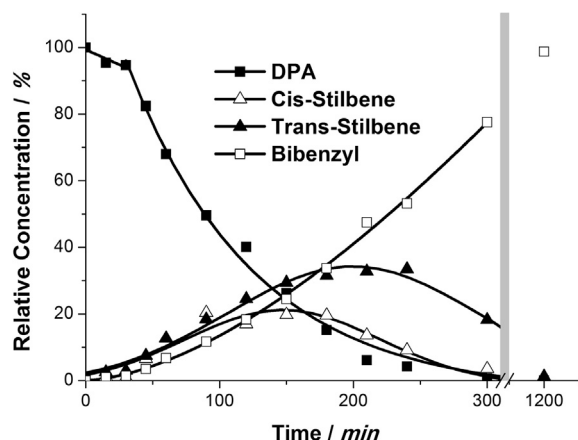


Fig. 3. Concentrations during hydrogenation of DPA performed with cyclohexane as a solvent. Reaction performed under 100 bar H_2 pressure, at 150 °C, with a catalyst loading of 270 mg (1 mmol of $NaAlH_4$) and 5 mmol of DPA.

lower limit and a more realistic estimate. The lower limit is based on the assumption that all of the BET surface areas measured by nitrogen physisorption are composed of available catalytically active sites. A more realistic estimation was made by using the volume fraction of $NaAlH_4$ in the catalyst, and assuming that the fraction of the total surface area consisting of $NaAlH_4$ was the same as the volume fraction of $NaAlH_4$ (see supporting information Section S4 for further details). The turnover frequency has been estimated to be 2 or 179 h^{-1} for the lower and more realistic estimate respectively. Although significantly lower than a typical Pd-based catalyst, these values are comparable to those for Frustrated Lewis Pair catalysts [13]. The alkyne functionality in the DPA is fully reduced to the alkane (bibenzyl) by the catalyst. This demonstrates that the catalyst can in fact hydrogenate both alkynes and alkenes.

Fig. 4 shows the dependence of the rate of the DPA consumption on catalyst loading. Each point was generated by performing the reaction for 2 h with samples being taken every 10 min for GC analysis. In this way the rate of DPA consumption up to 50% was determined accurately for each catalyst loading. The rate increases linearly with catalyst loading. Since there is a small amount of DPA conversion in the absence of catalyst it is possible that the metals in the walls of the autoclave, in which the reaction is carried out,

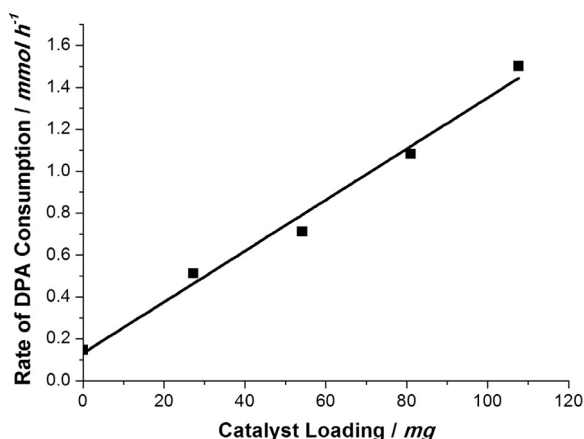


Fig. 4. Average rate of DPA hydrogenation versus catalyst loading in cyclohexane. Each data point was determined from the time taken to reach 50% conversion of DPA. All experiments were performed at 150 °C, 100 bar H_2 with GC samples taken every 10 min for 2 h.

are at least partially responsible for the observed activity of the $NaAlH_4/C$ catalyst. To rule this out the reaction was also performed with a Teflon insert in the autoclave (Fig. S2.1). When the Teflon liner is used the activity is 2.32 mol (DPA) mol^{-1} ($NaAlH_4$) h^{-1} , which is only a 1% deviation from the activity seen when the Teflon insert is not used. Further, the carbon support itself showed no effect on the rate of DPA hydrogenation (see supporting information Section S2). Therefore it can be concluded that the metals in the autoclave walls and the carbon support are not the source of the apparent catalytic activity of the $NaAlH_4/C$ catalyst.

To determine recyclability of the catalyst a reaction was performed at 150 °C, 100 bar hydrogen pressure in a cyclohexane solvent with a catalyst loading of 270 mg and DPA loading of 5 mmol. After the reaction was finished the catalyst was recovered by filtration, dried and used again in a hydrogenation reaction under the same conditions (Fig. 5). In the second run 150 mg of the catalyst was recovered so the amount of catalyst was 44% lower. This is reflected in the data as the rate of hydrogenation is 53% slower in the second run.

In order to further determine the scope of the catalyst a number of other substrates were also tested under the same conditions (Table 1, see supporting information Section S5 for reaction profiles). 1-octyne and 4-octyne were chosen as they are unfunctionalized alkynes and can demonstrate whether the catalyst is able to reduce terminal and internal alkynes respectively. Here it is clear that the catalyst can effectively reduce the unfunctionalized molecules and is more effective in reducing internal alkynes than terminal alkynes. This is also true for the resulting alkenes, which are further reduced to alkanes, demonstrating the ability of the catalyst to also reduce unfunctionalized alkenes. Hydrogenation of a conjugated alkene, styrene, further demonstrates the wide scope of the applicability of the catalyst.

3.3. Solvent effects

In previous literature [27] the hydrogenation of DPA was performed in toluene, and for this reason toluene was also used as a solvent for comparison to cyclohexane (Fig. 6). In toluene 50% conversion of DPA is achieved in roughly 350 min (activity of 0.48 mol (DPA) mol^{-1} ($NaAlH_4$) h^{-1}) whereas the same conversion when cyclohexane is employed occurs around 90 min (2.29 mol (DPA) mol^{-1} ($NaAlH_4$) h^{-1}), which is comparable to that for a Ti-doped ball-milled $NaAlH_4$ catalyst under similar conditions.

The solvent-dependence of the activity is striking and may be a result of either differences in hydrogen solubility or interaction with the catalyst. At room temperature the solubility of hydrogen in cyclohexane is 35% higher than for toluene at a pressure of 44 bar [30], but this can only account for a small portion of the difference in activity. Therefore it is very likely that something other than hydrogen solubility is affecting activity, such as competitive adsorption from the solvent. To verify this hypothesis we performed experiments on the adsorption of each substrate onto the catalyst surface in both solvents (Table 2. Details of the experiments and calculations can be found in S6 of the supporting information). They showed that there is a higher level of substrate adsorption in cyclohexane compared with toluene. Therefore, it can be inferred that toluene strongly adsorbs onto the catalyst surface, hindering the adsorption and subsequent reaction of DPA.

3.4. Selectivity control

The catalyst favors the production of *trans*-stilbene, which is not surprising as *trans*-stilbene is the thermodynamically more stable isomer [31]. There are two possible explanations for this, either this is the intrinsic selectivity of the catalyst or isomerization of *cis*-stilbene to *trans*-stilbene during reaction is affecting the

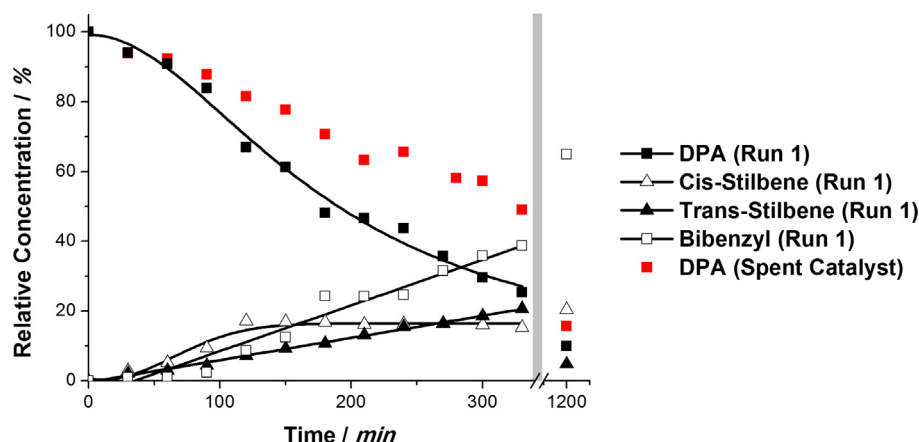


Fig. 5. Recyclability test of the NaAlH_4/C catalyst. The first run is shown in black and the run using the spent catalyst is shown in red. Conditions in both experiments: 150 °C, 100 bar H_2 , cyclohexane solvent, 5 mmol DPA. Samples taken every 30 min for 6 h, with one sample taken after roughly 20 h. (For interpretation of the references to color in this figure legend, the reader is referred to the web version of this article.)

Table 1

Conversion, yields and activities obtained when using the NaAlH_4/C nanocomposite as a hydrogenation catalyst for a number of substrates. Activities are given as the number of moles of hydrogenated substrate per hour, normalized to the total number of moles of NaAlH_4 in the NaAlH_4/C catalyst (roughly 1 mmol).

Substrate ^a	Conversion/%	Activity	Product	Yield/%
DPA	100	1.00	Cis-stilbene Trans-stilbene	0 0
1-Octyne	100	0.19	Bibenzyl 1-Octene	100 47
4-Octyne	95	0.23	Octane 4-Octene	43 2
Styrene	97	0.21	Octane Ethylbenzene	93 97

^a Reactions performed at 150 °C, 100 bar H_2 pressure for 48 h in a cyclohexane solvent, NaAlH_4 :substrate molar ratio of 1:5.

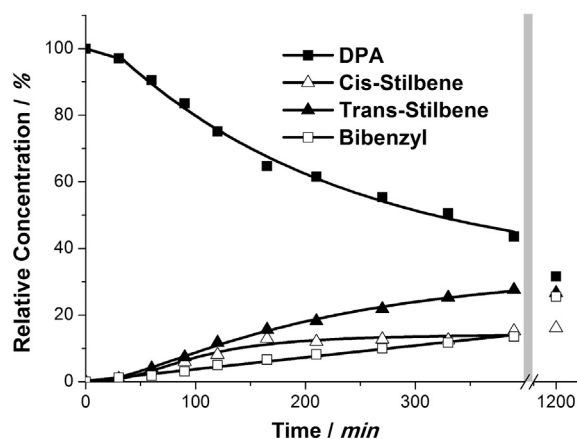


Fig. 6. Hydrogenation of DPA performed with toluene as a solvent. Each data point corresponds to a sample taken at the respective time and analyzed by gas chromatography. Reactions performed under 100 bar H_2 pressure, at 150 °C, with a catalyst loading of 270 mg (1 mmol of NaAlH_4) and 5 mmol of DPA.

observed selectivity. To verify this we monitored two separate reactions: hydrogenation of *trans*-stilbene and hydrogenation of *cis*-stilbene rather than DPA (Fig. 7). It was found that the rate of *trans*-stilbene formation from *cis*-stilbene is roughly 1.2 mmol h^{-1} whereas isomerization from *trans*- to *cis*-stilbene does not occur at all. This rate of isomerization can account for 100% of the *trans*-stilbene that is formed during reaction. Therefore, the catalyst primarily produces *cis*-stilbene through hydrogenation of DPA and *trans*-stilbene is only formed through isomerization of the *cis*-stilbene product.

Table 2

Summary of adsorption data for each substrate in cyclohexane and toluene.

Solvent	Substrate	Concentration drop after 60 min/%	% of catalyst surface coverage ^a
Cyclohexane	DPA	17.8	3.82 ± 0.03
	Cis-stilbene	16.0	4.04 ± 0.04
	Trans-stilbene	15.9	3.38 ± 0.02
	Bibenzyl	10.8	2.79 ± 0.03
Toluene	DPA	1.5	$0.35 \pm 0.00(2)$
	Cis-stilbene	1.9	0.82 ± 0.01
	Trans-stilbene	3.4	$0.61 \pm 0.00(4)$
	Bibenzyl	0.5	$0.10 \pm 0.00(03)$

^a Calculated from the BET surface area of the catalyst.

An interesting question given that isomerization of *cis*-stilbene can take place at the free surface of the catalyst is whether the number of active sites can affect the selectivity. Therefore a high molar DPA: NaAlH_4 ratio of 25:1 was applied, by reducing the catalyst loading (Fig. 8). The lower loading drastically altered the selectivity, yielding a *cis*:*trans* ratio of 12 at 50% conversion compared to a ratio of 1 at the same conversion when the lower DPA: NaAlH_4 ratio of 5 is used. The reason for this is possibly blocking of the active site required for isomerization by DPA at lower catalyst loadings. In any case the fact that the catalyst loading has such a marked impact on the selectivity demonstrates that this is not thermal isomerization. Compared to the more active Pd catalysts this provides the unique opportunity to tune selectivity by changing catalyst loading.

In order to gain more insight into the mode of action of the catalyst, particularly whether hydrogen can be directly extracted from the NaAlH_4 lattice or whether it is provided by the gas phase only,

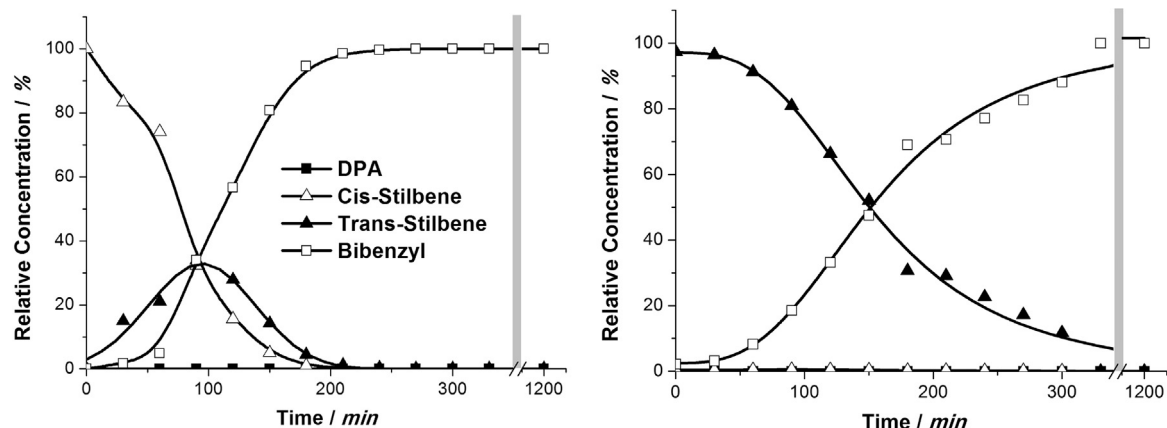


Fig. 7. Hydrogenation of *cis*-stilbene (left) and *trans*-stilbene (right) to determine the effect the catalyst has on isomerization of *cis*-stilbene and its reversibility. Conditions: 150 °C, 100 bar H₂, cyclohexane solvent, 270 mg catalyst (1 mmol NaAlH₄), 5 mmol *cis*-/ *trans*-stilbene.

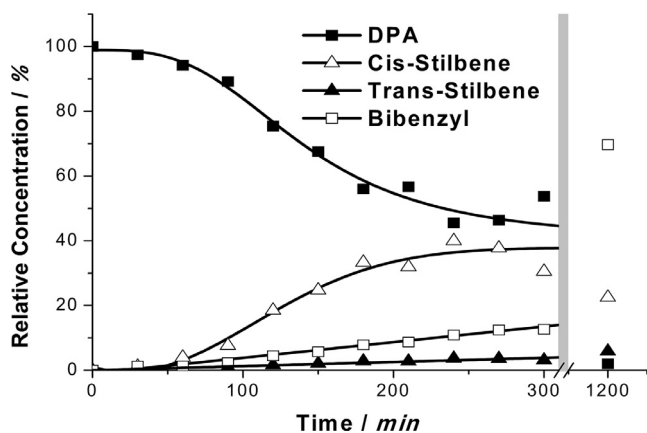


Fig. 8. Hydrogenation of DPA performed with a catalyst loading of 54 mg (0.2 mmol NaAlH₄) and 5 mmol DPA. 150 °C, 100 bar hydrogen, cyclohexane solvent.

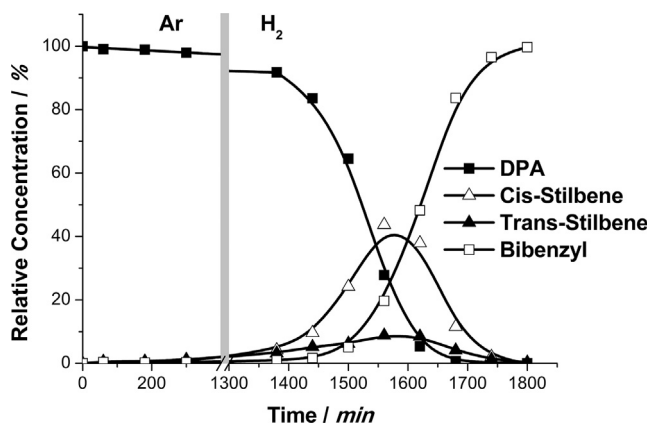


Fig. 9. Hydrogenation of DPA in the absence of gaseous hydrogen until 1400 min where hydrogen pressure was applied. The reaction was performed in cyclohexane at 150 °C with 80 bar Ar pressure initially before switching to 100 bar H₂ pressure. A DPA:NaAlH₄ molar ratio of 5:1 was used.

the catalyst was tested in the absence of gaseous hydrogen (Fig. 9). Hydrogenation occurs in the absence of gaseous hydrogen. This demonstrates that hydrogenation can proceed via extraction of hydrogen from the NaAlH₄ lattice. However, the rate of hydrogenation is low; reaching less than 10% conversion of DPA in 24 h, which corresponds to the consumption of 18% of the hydrogen in

the catalyst. Once hydrogen pressure is introduced, the reaction proceeds much more rapidly to 100% conversion to bibenzyl (BB) within 6 h. Possibly the extraction of hydrogen leads to a change in the nanostructure of the material (increasing the accessibility of the active sites) or an intrinsic change in the nature of the active sites.

Interestingly, if the hydrogen gas is introduced after a hydrogen-free period the catalyst is more selective toward *cis*-stilbene than when hydrogen is introduced at the start of the reaction. At 50% conversion the *cis*:*trans* ratio is 5, which is a fivefold increase compared to the reaction shown in Fig. 3. There are two possible explanations for this, the first being the aforementioned altered active surface area resulting from dehydrogenation of the catalyst. The other is that the intrinsic properties of the catalyst are changed during the Ar stage. However, in order to better understand this further investigation is required.

4. Conclusions

In conclusion, a transition-metal-free catalyst for hydrogenation of terminal and internal alkynes and alkenes has been demonstrated which consists of carbon supported NaAlH₄ using a carbon aerogel type support. The catalyst has the ability to hydrogenate a number of substrates, including conjugated systems and unfunctionalized molecules. Activity depends on solvent due to competitive adsorption effects on the catalyst surface, as confirmed experimentally. Using cyclohexane as a solvent the activity for DPA hydrogenation is 1 mol (DPA) mol⁻¹ (NaAlH₄) h⁻¹ at 150 °C. In contrast to typically used Pd catalysts the selectivity is 12 times higher in favor of the *cis*-stilbene intermediate at low catalyst loadings.

Additionally, we have shown that hydrogenation can occur via direct hydrogen extraction from the NaAlH₄ lattice. When the catalyst is partially dehydrogenated before addition of hydrogen gas pressure, selectivity is 5 times higher toward *cis*-stilbene than when hydrogen pressure is applied at the beginning of the reaction. As this new type of catalyst is based solely on light and abundant elements and does not contain any transition metals, yet can still display high selectivity toward the *cis*-alkene, it promises a new avenue in the development of catalysts for selective hydrogenation.

Author contributions

The manuscript was written through contributions of all authors. All authors have given approval to the final version of the manuscript.

The Project has been conceived by Petra de Jongh. Experimental work was carried out by Peter Bramwell, Jinbao Gao and Bernd de Waal. The major part of the text has been written by Peter Bramwell with significant contributions from Petra de Jongh, Krijn de Jong and Robertus Klein Gebbink.

Funding sources

This work was supported by the Netherlands Organization for Scientific Research [NWO-ECHO Grant No. 712.012.004].

Notes

The authors declare no competing financial interests.

Acknowledgment

The authors thank the financial support of the Netherlands Organisation for Scientific Research (NWO-ECHO grant). The authors would also like to thank Rien van Zwienen and Ad Mens for technical support and Dr. Michael Felderhoff of the Max-Planck-Institut für Kohlenforschung for the stimulating discussions.

Appendix A. Supplementary material

Supplementary data associated with this article can be found, in the online version, at <http://dx.doi.org/10.1016/j.jcat.2016.09.024>.

References

- [1] X. Cui, K. Burgess, *Chem. Rev.* 105 (2005) 3272–3296.
- [2] D.-S. Wang, Q.-A. Chen, S.-M. Lu, Y.-G. Zhou, *Chem. Rev.* 112 (2012) 2557–2590.
- [3] J.-H. Xie, S.-F. Zhu, Q.-L. Zhou, *Chem. Rev.* 111 (2011) 1713–1760.
- [4] P. Hauwert, G. Maestri, J.W. Sprengers, M. Catellani, *C.J. Elsevier, Angew. Chem.* 47 (2008) 3223–3226.
- [5] J.W. Sprengers, J. Wassenaar, N.D. Clement, K.J. Cavell, C.J. Elsevier, *Angew. Chem.* 44 (2005) 2026–2029.
- [6] M.W. van Laren, C.J. Elsevier, *Angew. Chem. Int. Ed.* 38 (1999) 3715–3717.
- [7] P. Hauwert, R. Boerleider, S. Warsink, J.J. Weigand, C.J. Elsevier, *J. Am. Chem. Soc.* 132 (2010) 16900–16910.
- [8] A.M. Kluwer, T.S. Koblenz, T. Jonischkeit, K. Woelk, C.J. Elsevier, *J. Am. Chem. Soc.* 127 (2005) 15470–15480.
- [9] H. Lindlar, *Helv. Chim. Acta* 35 (1952) 446–450.
- [10] E.V. Starodubtseva, M.G. Vinogradov, O.V. Turova, N.A. Bumagin, E.G. Rakov, V. I. Sokolov, *Catal. Commun.* 10 (2009) 1441–1442.
- [11] D. Teschner, J. Borsodi, A. Wootsch, Z. Révay, M. Hävecker, A. Knop-Gericke, S. D. Jackson, R. Schlögl, *Science* 320 (2008) 86–89.
- [12] M. García-Mota, B. Bridier, J. Pérez-Ramírez, N. López, *J. Catal.* 273 (2010) 92–102.
- [13] K. Chernichenko, A. Madarász, I. Pápai, M. Nieger, M. Leskelä, T. Repo, *Nat. Chem.* 5 (2013) 718–723.
- [14] D.W. Stephan, G. Erker, *Angew. Chem. Int. Ed.* 49 (2010) 46–76.
- [15] L.J. Hounjet, D.W. Stephan, *Org. Process Res. Dev.* 18 (2014) 385–391.
- [16] G. Kreiselmeier, W. Frey, B. Föhlisch, *Tetrahedron* 62 (2006) 6029–6035.
- [17] A.T. Tran, V.A. Huynh, E.M. Friz, S.K. Whitney, D.B. Cordes, *Tetrahedron Lett.* 50 (2009) 1817–1819.
- [18] G. Streukens, F. Schüth, *J. Alloys Compd.* 474 (2009) 57–60.
- [19] E.H. Majzoub, F. Zhou, V. Ozolinš, *J. Phys. Chem. C* 115 (2011) 2636.
- [20] S. Zheng, Y. Li, F. Fang, G. Zhou, X. Yu, G. Chen, D. Sun, L. Ouyang, M. Zhu, *J. Mater. Res.* 25 (2010) 2047.
- [21] J. Gao, P. Ngene, I. Lindemann, O. Gutfleisch, K.P. de Jong, P.E. de Jongh, *J. Mater. Chem.* 22 (2012) 13209.
- [22] J. Gao, P. Adelhelm, M.H.W. Verkuijen, C. Rongeat, M. Herrich, P.J.M. van Bentum, O. Gutfleisch, A.P.M. Kentgens, K.P. de Jong, P.E. de Jongh, *J. Phys. Chem. C* 114 (2010) 4675–4682.
- [23] M.H.W. Verkuijen, J. Gao, P. Adelhelm, P.J.M. van Bentum, P.E. de Jongh, A.P.M. Kentgens, *J. Phys. Chem. C* 114 (2010) 4683–4692.
- [24] P. Adelhelm, K.P. de Jong, P.E. de Jongh, *Chem. Commun.* (2009) 6261–6263.
- [25] Y.S. Au, M. Klein Obbink, S. Srinivasan, P.C.M.M. Magusin, K.P. de Jong, P.E. de Jongh, *Adv. Funct. Mater.* 24 (2014) 3604–3611.
- [26] P. Ngene, P. Adelhelm, A.M. Beale, K.P. de Jong, P.E.J. de Jongh, *Phys. Chem. C* 114 (2010) 6163–6168.
- [27] P. Ngene, R. van den Berg, M.H.W. Verkuijen, K.P. de Jong, P.E. de Jongh, *Energy Environ. Sci.* 4 (2011) 4108.
- [28] B. Bogdanović, R.A. Brand, A. Marjanovic, M. Schwickardi, J. Tölle, *J. Alloys Compd.* 302 (2000) 36–58.
- [29] S.A. Al-Muhtaseb, J.A. Ritter, *Adv. Mater.* 15 (2003) 101–114.
- [30] T. Tomoya, S. Yoshiko, H. Toshihiko, I. Naotsugu, *Fluid Phase Equilib.* 228–229 (2005) 499–503.
- [31] J.K. Rice, A.P. Baronavski, *J. Phys. Chem.* 96 (1992) 3359–3366.