

ARTICLE

Open Access

# Quenching of the red $\text{Mn}^{4+}$ luminescence in $\text{Mn}^{4+}$ -doped fluoride LED phosphors

Tim Senden<sup>1</sup>, Relinde J.A. van Dijk-Moes<sup>2</sup> and Andries Meijerink<sup>1</sup>

## Abstract

Red-emitting  $\text{Mn}^{4+}$ -doped fluorides are a promising class of materials to improve the color rendering and luminous efficacy of white light-emitting diodes (w-LEDs). For w-LEDs, the luminescence quenching temperature is very important, but surprisingly no systematic research has been conducted to understand the mechanism for thermal quenching in  $\text{Mn}^{4+}$ -doped fluorides. Furthermore, concentration quenching of the  $\text{Mn}^{4+}$  luminescence can be an issue but detailed investigations are lacking. In this work, we study thermal quenching and concentration quenching in  $\text{Mn}^{4+}$ -doped fluorides by measuring luminescence spectra and decay curves of  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$  between 4 and 600 K and for  $\text{Mn}^{4+}$  concentrations from 0.01% to 15.7%. Temperature-dependent measurements on  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$  and other  $\text{Mn}^{4+}$ -doped phosphors show that quenching occurs through thermally activated crossover between the  ${}^4\text{T}_2$  excited state and  ${}^4\text{A}_2$  ground state. The quenching temperature can be optimized by designing host lattices in which  $\text{Mn}^{4+}$  has a high  ${}^4\text{T}_2$  state energy. Concentration-dependent studies reveal that concentration quenching effects are limited in  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$  up to 5%  $\text{Mn}^{4+}$ . This is important, as high  $\text{Mn}^{4+}$  concentrations are required for sufficient absorption of blue LED light in the parity-forbidden  $\text{Mn}^{4+}$   $d-d$  transitions. At even higher  $\text{Mn}^{4+}$  concentrations (>10%), the quantum efficiency decreases, mostly due to direct energy transfer to quenching sites (defects and impurity ions). Optimization of the synthesis to reduce quenchers is crucial for developing more efficient highly absorbing  $\text{Mn}^{4+}$  phosphors. The present systematic study provides detailed insights into temperature and concentration quenching of  $\text{Mn}^{4+}$  emission and can be used to realize superior narrow-band red  $\text{Mn}^{4+}$  phosphors for w-LEDs.

## Introduction

White light-emitting diodes (w-LEDs) are the next-generation light sources for display and illumination systems because of their small size, high luminous efficacy, and long operation lifetime<sup>1–5</sup>. Conventional w-LEDs are composed of blue-emitting (In,Ga)N LEDs and green/yellow-emitting and orange/red-emitting phosphors that convert part of the blue LED emission<sup>5–7</sup>. Both phosphors are necessary to generate warm white light with a high color rendering index (CRI > 85). The typical red phosphors in w-LEDs are  $\text{Eu}^{2+}$ -doped nitrides (e.g.,  $\text{CaAlSiN}_3:\text{Eu}^{2+}$ )<sup>4,8</sup>. These phosphors exhibit high photoluminescence (PL) quantum efficiencies (QEs > 90%), but

their use also has a serious drawback. The  $\text{Eu}^{2+}$  emission band is broad and extends into the deep red spectral region ( $\lambda > 650$  nm) where the eye sensitivity is low. This causes the luminous efficacy of the w-LED to drop (reduced lumen/W output). A worldwide search is therefore aimed at finding efficient narrow-band red-emitting phosphors that can be excited by blue light. In this search,  $\text{Mn}^{4+}$ -doped fluoride phosphors, such as  $\text{K}_2\text{SiF}_6:\text{Mn}^{4+}$  and  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$ , have recently attracted considerable attention<sup>9–13</sup>. Under blue light excitation,  $\text{Mn}^{4+}$ -doped fluorides show narrow red line emission ( $\lambda_{\text{max}} \sim 630$  nm) with high luminescence QEs<sup>13–16</sup>. Furthermore, they are prepared through low-cost, simple wet-chemical synthesis at room temperature<sup>11,17</sup>. These aspects make  $\text{Mn}^{4+}$ -doped fluorides very promising red-emitting phosphors for developing energy-efficient high color-rendering w-LED systems<sup>9</sup>.

Correspondence: Tim Senden (t.senden@uu.nl)


<sup>1</sup>Condensed Matter and Interfaces, Debye Institute for Nanomaterials Science, Utrecht University, P.O. Box 80000, 3508 TA Utrecht, The Netherlands

<sup>2</sup>Soft Condensed Matter, Debye Institute for Nanomaterials Science, Utrecht University, P.O. Box 80000, 3508 TA Utrecht, The Netherlands

© The Author(s) 2018



**Open Access** This article is licensed under a Creative Commons Attribution 4.0 International License, which permits use, sharing, adaptation, distribution and reproduction in any medium or format, as long as you give appropriate credit to the original author(s) and the source, provide a link to the Creative Commons license, and indicate if changes were made. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in a credit line to the material. If material is not included in the article's Creative Commons license and your intended use is not permitted by statutory regulation or exceeds the permitted use, you will need to obtain permission directly from the copyright holder. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>.

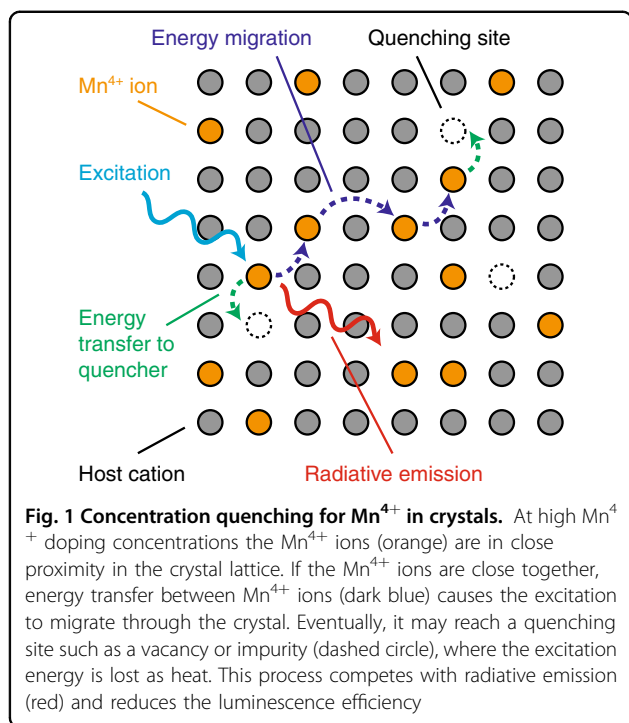

The application of Mn<sup>4+</sup>-doped fluoride phosphors in w-LEDs may, however, be hampered by thermal quenching of the Mn<sup>4+</sup> luminescence. Thermal quenching of the phosphor luminescence is a serious issue, as it affects both the efficacy and color stability of the w-LED. In high-power w-LEDs, the temperature of the on-chip phosphor layer easily reaches 450 K. At these elevated temperatures, thermal quenching occurs for Mn<sup>4+</sup>-doped fluorides. The luminescence quenching temperature  $T_{1/2}$ , the temperature at which the emission intensity is reduced to half of its maximum, is typically between 400 and 500 K<sup>15,18,19</sup>. Although the temperature dependence of the emission intensity has been measured for many Mn<sup>4+</sup>-doped fluorides, the understanding of the thermal quenching behavior is still limited. Most studies do not explain which process quenches the Mn<sup>4+</sup> luminescence<sup>13,20–23</sup>. Moreover, the few reports that do propose a quenching mechanism disagree. Paulusz<sup>15</sup> states that the luminescence of Mn<sup>4+</sup>-doped fluorides is quenched by thermally activated crossing of the Mn<sup>4+</sup> <sup>4</sup>T<sub>2</sub> excited state and <sup>4</sup>A<sub>2</sub> ground state. In contrast, Dorenbos<sup>24</sup> finds a relation between the quenching temperature and the energy of the F<sup>-</sup> → Mn<sup>4+</sup> charge-transfer (CT) state and therefore suggests that quenching involves crossover between the CT state and <sup>4</sup>A<sub>2</sub> ground state. This CT state crossover mechanism was also used by Blasse and our group to explain thermal quenching in Mn<sup>4+</sup>-doped oxides<sup>25–27</sup>. Finally, other reports claim that the quenching temperature increases if the radius of the cation substituted by Mn<sup>4+</sup> becomes smaller<sup>11,18</sup>. A better

understanding of the thermal quenching behavior is essential for developing Mn<sup>4+</sup>-doped fluoride phosphors with superior quenching temperatures, and thereby improving their potential for application in w-LEDs.

Besides thermal quenching, concentration quenching is an issue for the application of Mn<sup>4+</sup>-doped fluorides in w-LEDs. As the Mn<sup>4+</sup> *d-d* transitions are parity-forbidden, high Mn<sup>4+</sup> doping concentrations (e.g., 5 mol%) are required for sufficient absorption of the blue LED light<sup>12</sup>. At high dopant concentrations, energy migration among the Mn<sup>4+</sup> ions can result in concentration quenching<sup>26,28</sup>, as is illustrated in Fig. 1. If the distance between the Mn<sup>4+</sup> ions is small, excitation energy may efficiently migrate from one Mn<sup>4+</sup> ion to another until it reaches a quenching site (defect or impurity ion), where the excitation energy is lost non-radiatively (as heat). Studies on concentration quenching in Mn<sup>4+</sup>-doped fluorides are limited. Several works have compared the luminescence properties of fluoride phosphors with varying Mn<sup>4+</sup> concentrations, but do not measure the actual Mn<sup>4+</sup> concentration in the phosphors by elemental analysis<sup>29–33</sup>. Determining the Mn<sup>4+</sup> concentration is crucial, as often only a fraction of the Mn<sup>4+</sup> ions is incorporated during the synthesis<sup>19,34</sup>. Reports that do perform elemental analysis study only a small range of Mn<sup>4+</sup> doping concentrations and do not provide insight into the role of concentration quenching in Mn<sup>4+</sup> doped fluorides<sup>13,35,36</sup>. An in-depth investigation of concentration quenching in Mn<sup>4+</sup>-doped fluorides is thus lacking, despite it being very important for the application of Mn<sup>4+</sup>-doped fluorides in w-LEDs.

In this work, we systematically investigate concentration quenching and thermal quenching in Mn<sup>4+</sup>-doped fluorides. The quenching is studied by measuring luminescence spectra and decay curves in the temperature range of 4 to 600 K for K<sub>2</sub>TiF<sub>6</sub>:Mn<sup>4+</sup> phosphors with Mn<sup>4+</sup> concentrations ranging from 0.01 to 15.7 mol% (actual Mn<sup>4+</sup> concentration). The temperature-dependent luminescence measurements of K<sub>2</sub>TiF<sub>6</sub>:Mn<sup>4+</sup> and other Mn<sup>4+</sup>-doped phosphors demonstrate that thermal quenching occurs because of thermally activated crossover from the <sup>4</sup>T<sub>2</sub> excited state to the <sup>4</sup>A<sub>2</sub> ground state. This insight into the quenching mechanism shows that the Mn<sup>4+</sup> quenching temperature can be raised by finding fluoride hosts that have an increased Mn<sup>4+</sup> <sup>4</sup>T<sub>2</sub> level energy. Concentration studies show that the luminescence QE of K<sub>2</sub>TiF<sub>6</sub>:Mn<sup>4+</sup> is high, ~80%, for doping concentrations up to 5 mol% Mn<sup>4+</sup>. Concentration quenching is limited for these relatively high Mn<sup>4+</sup> dopant concentrations. At even higher doping concentrations of >10 mol%, the QE of K<sub>2</sub>TiF<sub>6</sub>:Mn<sup>4+</sup> falls below 60%. Luminescence decay curves indicate that the drop in QE can be attributed to an increased probability for direct energy transfer to quenching sites

(e.g., defects, impurity ions,  $\text{Mn}^{2+}$ , and  $\text{Mn}^{3+}$ ), the concentration of which increases with the  $\text{Mn}^{4+}$  concentration. The present results provide an improved understanding of thermal quenching and concentration quenching in  $\text{Mn}^{4+}$ -doped solids and can be used to develop superior  $\text{Mn}^{4+}$ -doped fluoride phosphors for w-LEDs.

## Materials and methods

### Synthesis and characterization of $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$ phosphors

The  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$  ( $x\%$ ) phosphors were synthesized according to the method of Zhu et al.<sup>13</sup> For the synthesis of  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$  (0.8%), 0.0488 g of  $\text{K}_2\text{MnF}_6$  (prepared following refs. 37,38) was dissolved in 2.5 mL of a 40 wt% HF solution (Fluka, 40 wt% HF in water). Next, the obtained yellow-brown solution was mixed with 4.5730 g of  $\text{K}_2\text{TiF}_6$  (Sigma-Aldrich, p.a.) and then stirred for 1 h at room temperature to form  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$  crystals. The  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$  phosphor was isolated by decanting the HF solution, washing twice with 15 mL of ethanol and then drying the phosphor for 7 h at 75 °C. The other  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$  ( $x\%$ ) phosphors were prepared following the same procedure but using other amounts of  $\text{K}_2\text{MnF}_6$  and  $\text{K}_2\text{TiF}_6$  as to obtain different  $\text{Mn}^{4+}$  doping concentrations.

Powder X-ray diffraction (see Supplementary Figure S1) confirms that the  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$  ( $x\%$ ) phosphors exhibit the hexagonal crystal structure of  $\text{K}_2\text{TiF}_6$  up to the highest doping concentration of 15.7%  $\text{Mn}^{4+}$ . Furthermore, no impurities of  $\text{K}_2\text{MnF}_6$  or other crystal phases are observed in the diffraction patterns. Scanning electron microscopy (SEM) images show that most  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$  phosphor particles are irregularly shaped and have sizes ranging from 1 to 200  $\mu\text{m}$  (see Supplementary Figure S2a). Some particles have a hexagonal shape, in agreement with the hexagonal crystal structure of  $\text{K}_2\text{TiF}_6$  (see Supplementary Figure S2b). Energy-dispersive X-ray (EDX) spectra (see Supplementary Figure S2c) confirm that the phosphor particles consist of potassium, titanium, fluorine, and manganese ions. The manganese dopant concentrations in the  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$  phosphors were determined with inductively coupled plasma optical emission spectroscopy (ICP-OES). The ICP-OES measurements were performed on a Perkin-Elmer Optima 8300DV spectrometer ( $\lambda_{\text{em}} = 257.61$  and 259.37 nm). For the ICP-OES analyses, the  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$  phosphors were dissolved in aqua regia.

### Optical spectroscopy

PL measurements were performed on an Edinburgh Instruments FLS920 fluorescence spectrometer, except for the PL decay measurements between 300 and 600 K (see below). For recording excitation and emission spectra, we used a 450 W Xe lamp as excitation source and a


Hamamatsu R928 photomultiplier tube (PMT) with a grating blazed at 500 nm for detection of emission. For PL decay measurements, excitation was done with a tunable optical parametric oscillator (OPO) Oportek Opolette HE 355II laser (pulse width 10 ns, repetition rate 10 Hz) and emission was detected with a Hamamatsu H74220–60 PMT. The PL decay curves between 300 and 600 K were recorded on a different setup, which had an Ekspla NT 342B OPO laser (pulse width 5 ns, repetition rate 10 Hz) as excitation source and a 0.55 m Triax 550 monochromator combined with a Hamamatsu H74220–60 PMT for detection of emission. All PL decay curves were obtained by multi-channel scaling (MCS) with a PicoQuant TimeHarp 260 computer card. The  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$  phosphors were cooled down to 4 K with an Oxford Instruments liquid helium flow cryostat. For PL measurements between 300 and 600 K samples were heated in a Linkam THMS600 temperature controlled stage. The PL quantum efficiencies of the phosphors were determined with a calibrated home-built setup, which consisted of a 65 W Xe lamp, excitation monochromator, integrating sphere (Labsphere) and CCD camera (Avantes AvaSpec-2048).

## Results and discussion

### Luminescence of $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$

For our quenching studies, we examine the luminescence of  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$  phosphors with a wide range of  $\text{Mn}^{4+}$  doping concentrations. A photographic image of the  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$  ( $x\%$ ) phosphors is displayed in Fig. 2a. The  $\text{Mn}^{4+}$  doping concentrations  $x$  (molar percentages with respect to  $\text{Ti}^{4+}$ ) were determined by inductively coupled plasma optical emission spectroscopy (ICP-OES). The body color of  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$  becomes more yellow with increasing  $\text{Mn}^{4+}$  concentration as a result of enhanced absorption in the blue. All of the investigated  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$  phosphors exhibit bright red  $\text{Mn}^{4+}$  luminescence under UV photoexcitation.

Figure 2b depicts the Tanabe–Sugano energy level diagram of  $\text{Mn}^{4+}$  ( $3d^3$  electron configuration) in an octahedral crystal field<sup>39,40</sup>. The diagram gives the  $d^3$  energy levels as a function of the crystal field splitting  $\Delta_{\text{O}}$ . Due to its high effective positive charge,  $\text{Mn}^{4+}$  experiences a strong crystal field and therefore the  ${}^2\text{E}$  state is the lowest energy excited state. Hence, the emission spectrum of  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$  (0.8%) is dominated by narrow red emission lines due to spin- and parity-forbidden  ${}^2\text{E} \rightarrow {}^4\text{A}_2$  transitions, as can be seen in Fig. 2c. The other  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$  ( $x\%$ ) phosphors exhibit similar emission spectra. As the potential energy curves of the  ${}^2\text{E}$  and  ${}^4\text{A}_2$  states are at the same equilibrium position, the  ${}^2\text{E} \rightarrow {}^4\text{A}_2$  emission is characterized by narrow zero-phonon and vibronic emission lines. The potential energy curves of the  ${}^2\text{E}$  and  ${}^4\text{A}_2$  states are at the same equilibrium position because

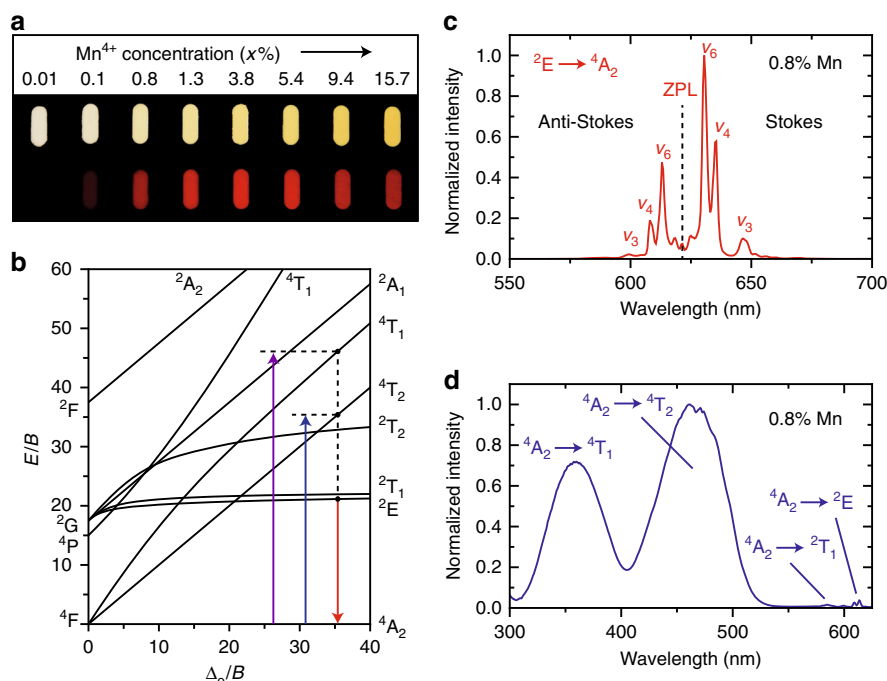

**Fig. 2**  $\text{Mn}^{4+}$  luminescence of  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$ . **a** Photographic image of  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$  (x%) phosphors with  $x = 0.01, 0.1, 0.8, 1.3, 3.8, 5.4, 9.4,$  and  $15.7$ . The phosphors have a white to yellow body color under ambient light (top) and show red  $\text{Mn}^{4+}$  luminescence under 365 nm UV illumination (bottom). **b** Tanabe–Sugano energy level diagram of the  $d^3$  electron configuration in an octahedral crystal field. The  ${}^4\text{A}_2 \rightarrow {}^4\text{T}_1$ ,  ${}^4\text{A}_2 \rightarrow {}^4\text{T}_2$ , and  ${}^2\text{E} \rightarrow {}^4\text{A}_2$  transitions of  $\text{Mn}^{4+}$  are indicated by the purple, blue and red arrows, respectively. Note that the excitation transitions are displaced for clarity. For a specific coordination all transitions take place around the same crystal field  $\Delta_o$ . **c** Emission spectrum of  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$  (0.8%) upon excitation with blue light ( $\lambda_{\text{exc}} = 450$  nm). **d** Excitation spectrum of the red  $\text{Mn}^{4+}$  luminescence ( $\lambda_{\text{em}} = 630$  nm) from  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$  (0.8%). Spectra are recorded at ambient temperature

the  ${}^2\text{E}$  and  ${}^4\text{A}_2$  states originate from the same  $t_{2g}^3$  electron configuration<sup>41</sup>.

The  ${}^2\text{E} \rightarrow {}^4\text{A}_2$  emission spectrum consists of a weak zero-phonon line (ZPL) at  $\sim 622$  nm and more intense anti-Stokes and Stokes vibronic emissions (labeled  $\nu_3$ ,  $\nu_4$ , and  $\nu_6$ ) on the high and low energy sides of the ZPL, respectively<sup>13,15</sup>. The ZPL is very weak because  $\text{Mn}^{4+}$  is located on a site with inversion symmetry in  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$ . Due to the inversion symmetry, there are no odd-parity crystal field components to admix opposite parity states into the  ${}^4\text{A}_2$  and  ${}^2\text{E}$  states and, as a result, the  ${}^2\text{E} \rightarrow {}^4\text{A}_2$  transition is electric dipole forbidden. The  ${}^2\text{E} \rightarrow {}^4\text{A}_2$  transition can become partly allowed, however, by coupling with asymmetric vibrations that induce odd-parity crystal field components. The most intense lines in Fig. 2c are assigned to  ${}^2\text{E} \rightarrow {}^4\text{A}_2$  transitions coupling with the asymmetric  $\nu_3$ ,  $\nu_4$ , and  $\nu_6$  vibrational modes (phonons) of the  $\text{MnF}_6^{2-}$  group. Thermal population of phonons at room temperature allows coupling with  $\nu_3$ ,  $\nu_4$ , and  $\nu_6$  phonon modes in the  ${}^2\text{E}$  excited state (giving rise to the anti-Stokes lines), while transitions to these phonon modes in the  ${}^4\text{A}_2$  ground state can occur at all temperatures (Stokes lines).

Figure 2d displays the excitation spectrum of the red  $\text{Mn}^{4+}$  luminescence from  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$ . The two broad excitation bands correspond to spin-allowed  ${}^4\text{A}_2 \rightarrow {}^4\text{T}_1$  and  ${}^4\text{A}_2 \rightarrow {}^4\text{T}_2$  transitions (violet and blue arrows in Fig. 2b). In addition, some weak peaks are visible around 600 nm. These peaks are assigned to  ${}^4\text{A}_2 \rightarrow {}^2\text{E}$  and  ${}^4\text{A}_2 \rightarrow {}^2\text{T}_1$  transitions. The  ${}^4\text{A}_2 \rightarrow {}^2\text{T}_1$ ,  ${}^2\text{E}$  transitions are spin-forbidden and therefore low in intensity compared to the spin-allowed  ${}^4\text{A}_2 \rightarrow {}^4\text{T}_1$ ,  ${}^4\text{T}_2$  transitions.

#### Temperature dependence of the $\text{Mn}^{4+}$ luminescence

To study the thermal quenching of the  $\text{Mn}^{4+}$  emission, we measure the PL intensity and  $\text{Mn}^{4+}$  emission lifetime of  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$  (0.01%) as a function of temperature between 4 and 600 K. We use a very low  $\text{Mn}^{4+}$  doping concentration of 0.01%, as for higher  $\text{Mn}^{4+}$  concentrations reabsorption of emission and energy transfer between  $\text{Mn}^{4+}$  ions can occur. These processes will influence (the temperature dependence of) the  $\text{Mn}^{4+}$  luminescence spectra and decay curves<sup>6</sup>. As a result, with a high concentration of  $\text{Mn}^{4+}$  ions, the observations may not reflect the intrinsic thermal quenching properties of  $\text{Mn}^{4+}$ .

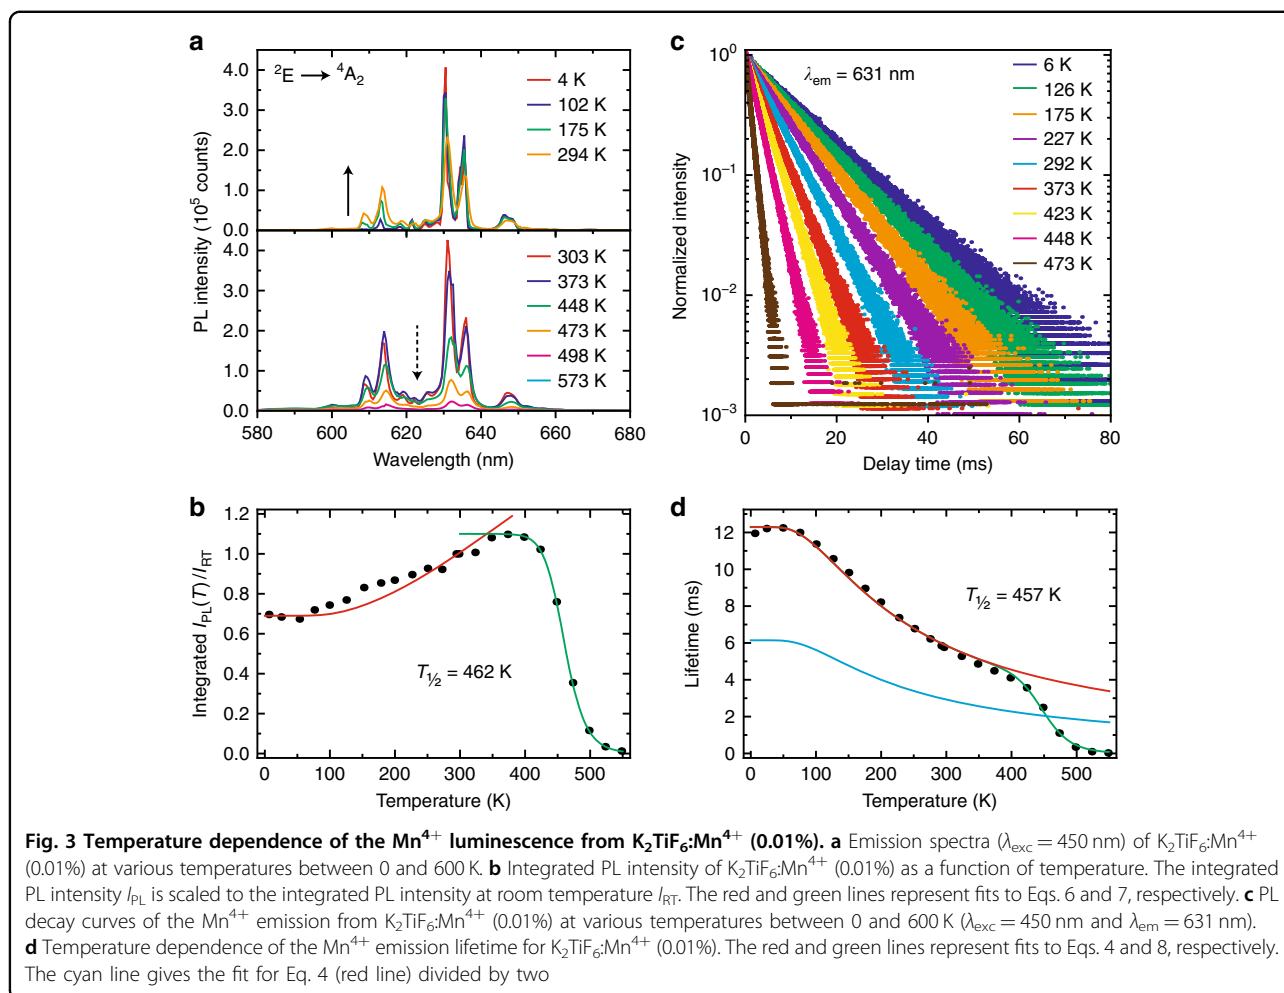


Figure 3a shows emission spectra of K<sub>2</sub>TiF<sub>6</sub>:Mn<sup>4+</sup> (0.01%) at various temperatures between 4 and 600 K. At 4 K the Mn<sup>4+</sup>  ${}^2\text{E} \rightarrow {}^4\text{A}_2$  emission spectrum consists of zero-phonon and Stokes vibronic lines. Upon raising the temperature, phonon modes are thermally populated and anti-Stokes emission lines appear (solid arrow in Fig. 3a). With the appearance of anti-Stokes lines, the relative intensity of the Stokes emission decreases between 4 and 300 K. Above 400 K the intensities of both the anti-Stokes and Stokes emission lines begin to decrease (dashed arrow in Fig. 3a), which indicates the onset of non-radiative transitions from the  ${}^2\text{E}$  excited state. The luminescence is quenched at 600 K. From the measurements, we obtain the temperature dependence of the integrated PL intensity ( $I_{\text{PL}}$ ) relative to the integrated PL intensity at room temperature ( $I_{\text{RT}}$ ) (Fig. 3b). The PL intensity of K<sub>2</sub>TiF<sub>6</sub>:Mn<sup>4+</sup> (0.01%) gradually increases between 4 and 350 K but then rapidly drops due to the onset of non-radiative transitions (luminescence quenching).

An alternative method to determine the luminescence quenching temperature is by measuring luminescence

decay times. Figure 3c shows a selection of PL decay curves of K<sub>2</sub>TiF<sub>6</sub>:Mn<sup>4+</sup> (0.01%) measured between 4 and 600 K. The decay of the Mn<sup>4+</sup> emission is single exponential and becomes faster with increasing temperature. The PL decay time is on the order of milliseconds, which is expected as the transition between the  ${}^2\text{E}$  and  ${}^4\text{A}_2$  states is both parity- and spin-forbidden. In Fig. 3d, the Mn<sup>4+</sup> emission lifetime (determined from single exponential fitting) is plotted as a function of temperature. The lifetime shows a steady decrease, starting above 50 K. The decrease levels off between 300 and 400 K but then shows a rapid decrease above 400 K.

The temperature dependences observed in Fig. 3b and d are quite exceptional. For most luminescent materials, the PL intensity and lifetime are relatively constant with temperature and both begin to decrease once thermal quenching sets in<sup>6,42,43</sup>. The PL intensity of K<sub>2</sub>TiF<sub>6</sub>:Mn<sup>4+</sup>, however, rises by 40% between 4 and 350 K while the lifetime decreases before thermal quenching takes place. To understand this peculiar temperature dependence, we first discuss how the radiative decay rate of the  ${}^2\text{E}$  state

changes with temperature. The  ${}^2E \rightarrow {}^4A_2$  emission of  $K_2TiF_6:Mn^{4+}$  mainly consists of anti-Stokes and Stokes vibronic emissions (Fig. 2c). Their transition probabilities increase with phonon population. The population of phonon modes is given by the phonon occupation number  $n$ , which increases with temperature according to<sup>41</sup>:

$$n = \frac{1}{\exp(h\nu/k_B T) - 1} \quad (1)$$

where  $k_B$  is the Boltzmann constant and  $h\nu$  is the energy of the phonon coupling to the  ${}^2E \rightarrow {}^4A_2$  transition. The transition probabilities  $P_R$  of the anti-Stokes and Stokes vibronics scale with  $n$  by:

$$\text{Anti - Stokes : } P_R(T) = P_R(0)[n] \quad (2)$$

$$\text{Stokes : } P_R(T) = P_R(0)[n + 1] \quad (3)$$

where  $P_R(0)$  is the transition probability at  $T = 0$  K. As the radiative lifetime  $\tau_R$  is proportional to  $1/[P_R(\text{anti-Stokes}) + P_R(\text{Stokes})]$ , it follows from Eqs. 1–3 that:

$$\tau_R(T) = \frac{\tau_R(0)}{\coth(h\nu/2k_B T)} \quad (4)$$

Here,  $\tau_R(0)$  is the radiative lifetime at  $T = 0$  K. In Fig. 3d, Eq. 4 (red line) has been plotted for  $\tau_R(0) = 12.3$  ms and  $h\nu = 216$   $\text{cm}^{-1}$  (phonon energy of the intense  $\nu_6$  mode emission). Equation 4 accurately describes the measured temperature dependence of the  $Mn^{4+}$  emission lifetime up to 375 K, confirming that the decay of the  ${}^2E$  state is mainly radiative up to this temperature. The radiative lifetime of the  $Mn^{4+}$  emission shortens with temperature due to thermal population of odd-parity vibrational modes at higher temperatures.

Next, we investigate the increase in PL intensity between 4 and 350 K. The PL intensity  $I_{PL}$  equals the product of the PL QE and number of absorbed photons (as  $I_{PL}$  scales with the number of absorbed photons, the excitation wavelength can have a large influence on the temperature dependence observed for  $I_{PL}$ ; see Supplementary Information). The PL QE  $\eta$  of  $K_2TiF_6:Mn^{4+}$  can be expressed as:

$$\eta = \frac{\gamma_R}{\gamma_R + \gamma_{NR}} \quad (5)$$

where  $\gamma_R$  and  $\gamma_{NR}$  are the radiative and non-radiative decay rates of the emitting  ${}^2E$  state, respectively. The results in Fig. 3d show that the decay of the  ${}^2E$  state is mainly radiative up to 375 K, so we can assume that  $\gamma_{NR}$  is negligible between 0 and 350 K. The value for  $\eta$  is therefore approximated as a constant close to unity between 0 and 350 K. On the other hand, the  ${}^4A_2 \rightarrow {}^4T_2$  absorption will change with temperature. Like the  ${}^2E \rightarrow {}^4A_2$  transition, the  ${}^4A_2 \rightarrow {}^4T_2$  transition is electric dipole (parity) forbidden and gains intensity by coupling

with vibrations (for more details on the vibronic structure of the  ${}^4A_2 \rightarrow {}^4T_2$  excitation band, see refs. 15,16,44). As a result, the PL intensity  $I_{PL}$  will scale with temperature as<sup>20,41,45</sup>:

$$I_{PL}(T) = I(0)\coth\left(\frac{h\nu}{2k_B T}\right) \quad (6)$$

with  $I(0)$  being the PL intensity at  $T = 0$  K. The results in Fig. 3b show that the increase in PL intensity between 4 and 350 K follows the temperature dependence given by Eq. 6. This confirms that the higher PL intensity at 350 K is due to a stronger absorption of excitation light. An increase in PL intensity between 4 and 350 K due to enhanced absorption is observed for all investigated  $Mn^{4+}$  doping concentrations (see Supplementary Information). Although the temperature dependence of the PL intensity follows Eq. 6, there is deviation between the fit of Eq. 6 and the measured data (see red line in Fig. 3b). The model of Eq. 6 is simple and does not take into account the shift and broadening of the  ${}^4A_2 \rightarrow {}^4T_2$  absorption band with temperature. Both these effects also influence the temperature dependence of the PL intensity, and this can explain the deviation between the model and the experimental data. Including the effect of a shift and broadening of the  ${}^4A_2 \rightarrow {}^4T_2$  band on the absorption strength is complex and will not aid a more accurate determination of  $T_{1/2}$ .

Above 400 K the PL intensity of  $K_2TiF_6:Mn^{4+}$  (0.01%) begins to decrease due to the onset of non-radiative transitions (Fig. 3a, b). The non-radiative decay probability rapidly increases with temperature above 400 K and as a result the luminescence is quenched, with no emission intensity remaining at 600 K. The quenching temperature  $T_{1/2}$  is determined to be 462 K. The  $Mn^{4+}$  emission lifetime also rapidly decreases once thermal quenching sets in (Fig. 3d). Above 400 K the  $Mn^{4+}$  emission lifetime is shorter than the radiative lifetime  $\tau_R$  predicted by Eq. 4 (red line). The lifetime shortens because of an additional thermally activated non-radiative contribution to the decay of the  ${}^2E$  state. From the temperature dependence of the lifetime,  $T_{1/2}$  can be determined by locating the temperature at which the lifetime has decreased to half of its radiative lifetime value. To estimate  $T_{1/2}$ , we divide the value from the fit of Eq. 4 for  $\tau_R$  by a factor of 2 (Fig. 3d, cyan line). The cyan line crosses the data points at 457 K. This value for  $T_{1/2}$  is very close to the  $T_{1/2}$  of 462 K obtained from the PL intensity measurements.

Thermal quenching can be described as a thermally activated process with an activation energy  $\Delta E$ . The activation energy is obtained by fitting a modified Arrhenius equation to the temperature dependence of the

PL intensity  $I_{\text{PL}}$  between 350 and 600 K<sup>43,46</sup>:


$$I_{\text{PL}}(T) = \frac{I(0)}{1 + A \times \exp(-\Delta E/k_B T)} \quad (7)$$

In Eq. 7,  $I(0)$  is the maximum PL intensity,  $k_B$  is the Boltzmann constant and  $A$  is a rate constant for the thermal quenching process. The best fit to Eq. 7 (green line in Fig. 3b) gives an activation energy  $\Delta E$  of 9143  $\text{cm}^{-1}$  and a rate constant  $A$  of  $2.5 \times 10^{12}$ . We can also determine  $\Delta E$  by fitting the temperature dependence of the  $\text{Mn}^{4+}$  emission lifetime  $\tau(T)$  to the following expression<sup>47</sup>:

$$\tau(T) = \frac{\tau_R(T)}{1 + \left(\frac{\tau_R(T)}{\tau_{\text{NR}}}\right) \exp(-\Delta E/k_B T)} \quad (8)$$

Here,  $1/\tau_{\text{NR}}$  is the non-radiative decay rate and  $\tau_R(T)$  is the radiative lifetime as described by Eq. 4 with  $\tau_R(0) = 12.3 \text{ ms}$  and  $h\nu = 216 \text{ cm}^{-1}$ . We fit Eq. 8 to the  $\text{Mn}^{4+}$  emission lifetimes (green line in Fig. 3d) and find an activation energy  $\Delta E$  of 7100  $\text{cm}^{-1}$  and a prefactor  $1/\tau_{\text{NR}}$  of  $1.5 \times 10^{12} \text{ s}^{-1}$ . On the basis of the two similar values for  $\Delta E$ , we conclude that the activation energy of the thermal

quenching process is  $\sim 8000 \text{ cm}^{-1}$ . The rate constants  $A$  and  $1/\tau_{\text{NR}}$  should be approximately equal to the vibrational frequencies of the  $\text{MnF}_6^{2-}$  group. The  $\nu_6$  vibrational mode has a frequency of  $6.5 \times 10^{12} \text{ s}^{-1}$ , close to the rate constants found by fitting the data to Eqs. 7 and 8. The variation in activation energy values and prefactors can be explained by the fact that thermal quenching is not a simple thermally activated process. Struck and Fonger have shown that the temperature dependence of a non-radiative process is accurately described by considering ground and excited state vibrational wave function overlap<sup>46,48</sup>. According to the Struck–Fonger model, the non-radiative process occurs through tunneling (crossover) from a vibrational level of the excited state to a high vibrational level of the ground state. The tunneling rate, i.e., the non-radiative decay rate, depends on the wave function overlap of the vibrational levels involved. The tunneling rate will be faster for a larger overlap between the wave functions and when the vibrational levels are in resonance. For the present discussion, analysis of the data using complex models such as the Struck–Fonger model is not relevant, but it is important to realize that the

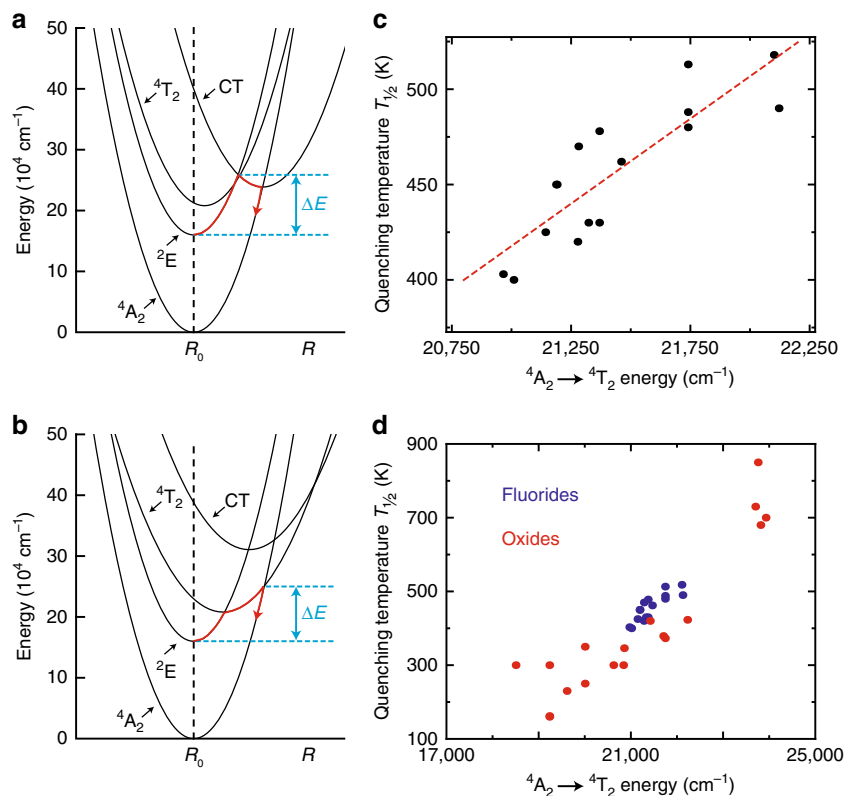

**Fig. 4 Thermal quenching in  $\text{Mn}^{4+}$ -doped fluorides.** **a, b** Configuration coordinate diagrams showing luminescence quenching due to **a** thermally activated crossover via the  $\text{F}^- \rightarrow \text{Mn}^{4+}$  charge-transfer (CT) state and **b** thermally activated crossover via the  $\text{Mn}^{4+} \ ^4\text{T}_2$  excited state. **c** Quenching temperature  $T_{1/2}$  of  $\text{Mn}^{4+}$ -doped fluoride phosphors as a function of the  $^4\text{A}_2 \rightarrow ^4\text{T}_2$  transition energy. The red dashed line is a linear fit to the data points. **d** Quenching temperature  $T_{1/2}$  of  $\text{Mn}^{4+}$ -doped fluorides (blue dots) and  $\text{Mn}^{4+}$ -doped oxides (red dots) as a function of the  $^4\text{A}_2 \rightarrow ^4\text{T}_2$  transition energy

Struck–Fonger model gives a more correct description of the actual quenching process.

### Thermal quenching in Mn<sup>4+</sup>-doped fluorides

To obtain insight into the thermal quenching of Mn<sup>4+</sup> luminescence, we will discuss four possible quenching processes: (1) multi-phonon relaxation, (2) thermally activated photoionization, (3) thermally activated crossover via the F<sup>-</sup> → Mn<sup>4+</sup> charge-transfer (CT) state, and (4) thermally activated crossover via the Mn<sup>4+</sup> <sup>4</sup>T<sub>2</sub> excited state.

In the configurational coordinate diagram, the parabolas of the Mn<sup>4+</sup> <sup>2</sup>E and <sup>4</sup>A<sub>2</sub> states do not cross and luminescence quenching by crossover from the <sup>2</sup>E to the <sup>4</sup>A<sub>2</sub> states is not possible (Fig. 4a). The <sup>4</sup>A<sub>2</sub> ground state may however be reached by multi-phonon relaxation. In Mn<sup>4+</sup>-doped fluorides more than 30 phonons of ~500 cm<sup>-1</sup> are needed to bridge the energy gap between the <sup>2</sup>E and <sup>4</sup>A<sub>2</sub> states<sup>49</sup>. For such high numbers of phonons ( $p > 30$ ), it is unrealistic that non-radiative multi-phonon relaxation is responsible for thermal quenching (see Supplementary Information for a more detailed discussion). Alternatively, the thermal quenching can be due to thermally activated photoionization of an electron from the Mn<sup>4+</sup> <sup>2</sup>E state to the fluoride host conduction band. Thermally activated photoionization typically quenches the emission from a luminescent center if the emitting state is close in energy to the host conduction band<sup>26,50</sup>. In density functional theory (DFT) calculations, large band gaps of around 8 eV have been found for fluoride hosts like K<sub>2</sub>SiF<sub>6</sub> and K<sub>2</sub>TiF<sub>6</sub><sup>51,52</sup>. It is therefore expected that the Mn<sup>4+</sup> <sup>2</sup>E state is well below the host conduction band levels. Based on this, we conclude that thermal quenching in Mn<sup>4+</sup>-doped fluorides is not caused by thermally activated photoionization. However, more evidence is necessary to exclude this quenching mechanism. Photoconductivity measurements on Mn<sup>4+</sup> phosphors at elevated temperatures need to be performed to provide convincing evidence for a possible role of photoionization in the thermal quenching of Mn<sup>4+</sup> emission.

Thermal quenching in Mn<sup>4+</sup>-doped fluorides has been suggested to occur by thermally activated crossover via the Mn<sup>4+</sup> <sup>4</sup>T<sub>2</sub> state or the F<sup>-</sup> → Mn<sup>4+</sup> charge-transfer (CT) state<sup>15,24,26</sup>. Both these states are displaced relative to the potential curve of the <sup>4</sup>A<sub>2</sub> ground state (Fig. 4a, b). Hence, the <sup>4</sup>T<sub>2</sub> and CT state parabolas cross the <sup>4</sup>A<sub>2</sub> ground state parabola. The difference between the potential curve equilibrium positions is given by the offset  $\Delta R = R_0' - R_0$ . By using the energies of the <sup>4</sup>A<sub>2</sub> → <sup>2</sup>E, <sup>4</sup>A<sub>2</sub> → <sup>4</sup>T<sub>2</sub> and <sup>4</sup>A<sub>2</sub> → CT transitions in K<sub>2</sub>TiF<sub>6</sub>:Mn<sup>4+</sup> (Fig. 2d and ref. <sup>13</sup>) and assuming specific offsets  $\Delta R$  for the <sup>4</sup>T<sub>2</sub> and CT states, we can construct the diagrams in Fig. 4a and b, where non-radiative relaxation occurs either via (a) the crossing of the CT and <sup>4</sup>A<sub>2</sub> states or (b) the

crossing of the <sup>4</sup>T<sub>2</sub> and <sup>4</sup>A<sub>2</sub> states. The offset of the CT state is typically larger than the offset of the <sup>4</sup>T<sub>2</sub> state. Note that the diagrams in Fig. 4a and b are schematic configuration coordinate diagrams to illustrate the different quenching mechanisms.

In Fig. 4a, the CT state has a larger offset  $\Delta R$  than the <sup>4</sup>T<sub>2</sub> state, which causes the CT parabola to cross the <sup>4</sup>A<sub>2</sub> parabola at lower energies than the <sup>4</sup>T<sub>2</sub> parabola. Thermal activation over the energy barrier  $\Delta E$  will allow crossover from the <sup>2</sup>E state into the CT state followed by non-radiative relaxation to the ground state via the crossing of the CT and <sup>4</sup>A<sub>2</sub> parabolas. Alternatively, thermal quenching of the Mn<sup>4+</sup> luminescence may be due to the mechanism depicted in Fig. 4b. Here, the CT state has a smaller offset  $\Delta R$  compared to that shown in Fig. 4a, and its potential curve is therefore at higher energies. In addition, the <sup>4</sup>T<sub>2</sub> state has a slightly larger offset. As a result, the crossing of the <sup>4</sup>T<sub>2</sub> and <sup>4</sup>A<sub>2</sub> parabolas is now at a lower energy and non-radiative relaxation will proceed via the crossing of the <sup>4</sup>T<sub>2</sub> and <sup>4</sup>A<sub>2</sub> parabolas.

The activation energies  $\Delta E$  in the configuration coordinate diagrams are ~8000 cm<sup>-1</sup>, similar to the  $\Delta E$  values obtained from the temperature-dependent measurements. This indicates that both mechanisms in Fig. 4a, b can explain the thermal quenching of Mn<sup>4+</sup> luminescence. To determine which of these two mechanisms is responsible for the luminescence quenching, we compare the quenching temperature  $T_{1/2}$  of K<sub>2</sub>TiF<sub>6</sub>:Mn<sup>4+</sup> to the  $T_{1/2}$  of other Mn<sup>4+</sup>-doped materials. A relation between the quenching temperature and the energy of either the CT or <sup>4</sup>T<sub>2</sub> state in a variety of hosts will give insight. If quenching occurs by crossover from the CT state to the <sup>4</sup>A<sub>2</sub> state,  $T_{1/2}$  will be higher for Mn<sup>4+</sup>-doped solids with higher CT transition energies. In K<sub>2</sub>TiF<sub>6</sub>:Mn<sup>4+</sup> and other Mn<sup>4+</sup>-doped fluorides the F<sup>-</sup> → Mn<sup>4+</sup> CT transition is at ~40,000 cm<sup>-1</sup><sup>113,15</sup>. Mn<sup>4+</sup>-doped oxides have lower O<sup>2-</sup> → Mn<sup>4+</sup> CT transition energies of 30,000–35,000 cm<sup>-1</sup> and are therefore expected to have lower  $T_{1/2}$  values than fluorides if quenching occurs by the mechanism in Fig. 4a<sup>26,27,53,54</sup>. Some Mn<sup>4+</sup>-doped oxides, however, have much higher quenching temperatures than Mn<sup>4+</sup>-doped fluorides. For example, Mg<sub>4</sub>GeO<sub>6</sub>:Mn<sup>4+</sup>, Mg<sub>28</sub>Ge<sub>7.5</sub>O<sub>38</sub>F<sub>10</sub>:Mn<sup>4+</sup>, and Mg<sub>6</sub>As<sub>2</sub>O<sub>11</sub>:Mn<sup>4+</sup> have a  $T_{1/2}$  of ~700 K<sup>55–57</sup>, while K<sub>2</sub>TiF<sub>6</sub>:Mn<sup>4+</sup> and other Mn<sup>4+</sup>-doped fluorides have a  $T_{1/2}$  of 400–500 K (see also Tables 1 and 2). No correlation is found between the Mn<sup>4+</sup> luminescence quenching temperature and the energy of the CT transition (see Supplementary Information for an overview and a plot of quenching temperatures and CT energies). From this we conclude that thermal quenching in Mn<sup>4+</sup>-doped fluorides is not caused by thermally activated crossover from the F<sup>-</sup> → Mn<sup>4+</sup> CT state to the <sup>4</sup>A<sub>2</sub> ground state.



**Table 1 Quenching temperature  $T_{1/2}$  (K) and  ${}^4A_2 \rightarrow {}^4T_2$  energy ( $\text{cm}^{-1}$ ) for  $\text{Mn}^{4+}$ -doped fluoride materials**


Host lattice	${}^4A_2 \rightarrow {}^4T_2$ energy ( $\text{cm}^{-1}$ )	$T_{1/2}$ (K)	References
$\text{K}_2\text{TiF}_6$	21,459	462	This work
$\text{K}_2\text{SiF}_6$	22,099	518	This work
$\text{K}_2\text{SiF}_6$	22,120	490	15
$\text{K}_2\text{GeF}_6$	21,280	470	15
$\text{K}_2\text{TiF}_6$	21,190	450	15
$\text{K}_2\text{TiF}_6$	21,368	478	13
$\text{Na}_2\text{SiF}_6$	21,739	488	21
$\text{Rb}_2\text{SiF}_6$	21,739	480	18
$\text{Rb}_2\text{TiF}_6$	21,186	450	18
$\text{Rb}_2\text{GeF}_6$	21,739	513	60
$\text{Cs}_2\text{GeF}_6$	21,277	420	22
$\text{Cs}_2\text{SiF}_6$	21,368	430	22
$\text{Cs}_2\text{HfF}_6$	20,964	403	44
$\text{BaSiF}_6$	21,322	430	23
$\text{BaSnF}_6$	21,008	400	45
$\text{BaTiF}_6$	21,142	425	61

**Table 2 Quenching temperature  $T_{1/2}$  (K) and  ${}^4A_2 \rightarrow {}^4T_2$  energy ( $\text{cm}^{-1}$ ) for  $\text{Mn}^{4+}$ -doped oxide materials**

Host lattice	${}^4A_2 \rightarrow {}^4T_2$ energy ( $\text{cm}^{-1}$ )	$T_{1/2}$ (K)	References
$\text{Mg}_4\text{GeO}_6$	23,697	730	55
$\text{Mg}_{28}\text{Ge}_{7.5}\text{O}_{38}\text{F}_{10}$	23,923	700	26,55,56
$\text{K}_2\text{Ge}_4\text{O}_9$	21,739	373	62
$\text{K}_2\text{Ge}_4\text{O}_9$ (site 1)	19,231	160	63
$\text{K}_2\text{Ge}_4\text{O}_9$ (site 2)	21,700	379	63
$\text{Rb}_2\text{Ge}_4\text{O}_9$ (site 1)	19,231	162	63
$\text{Rb}_2\text{Ge}_4\text{O}_9$ (site 2)	20,850	346	63
$\text{Y}_2\text{Mg}_3\text{Ge}_3\text{O}_{12}$	23,753	850	64
$\text{La}_3\text{GaGe}_5\text{O}_{16}$	21,413	420	65
$\text{La}_2\text{ZnTiO}_6$	19,608	230	66
$\text{La}_2\text{MgTiO}_6$	20,000	250	66
$\text{CaZrO}_3$	18,500	300	25,26
$\text{Mg}_6\text{As}_2\text{O}_{11}$	23,810	680	57
$\text{Y}_3\text{Al}_5\text{O}_{12}$	20,619	300	67
$\text{Y}_3\text{Al}_5\text{O}_{12}$	20,833	300	68
$\text{Sr}_4\text{Al}_{14}\text{O}_{25}$	22,222	423	69
$\text{SrLaAlO}_4$	19,231	300	53
$\text{LiGa}_5\text{O}_8$	20,000	350	70

Alternatively, thermal quenching of the  $\text{Mn}^{4+}$  luminescence can be caused by thermally activated crossover via the  $\text{Mn}^{4+} {}^4T_2$  excited state (Fig. 4b). To investigate the validity of this mechanism, we compare the  $T_{1/2}$  and  ${}^4A_2 \rightarrow {}^4T_2$  transition energies for  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$  and a variety of other  $\text{Mn}^{4+}$ -doped fluorides. From the literature and measurements on  $\text{Mn}^{4+}$  luminescence we have collected quenching temperatures and luminescence spectra, preferably for systems with low doping concentrations. Figures 2d and 3b show that  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$  has a  ${}^4A_2 \rightarrow {}^4T_2$  energy of  $21,459 \text{ cm}^{-1}$  (maximum of the excitation band) and a  $T_{1/2}$  of 462 K. For  $\text{K}_2\text{SiF}_6:\text{Mn}^{4+}$ , we measured a  ${}^4A_2 \rightarrow {}^4T_2$  energy of  $22,099 \text{ cm}^{-1}$  and a  $T_{1/2}$  of 518 K (Supplementary Figure S6,  $\text{K}_2\text{SiF}_6:\text{Mn}^{4+}$  BR301-C commercial phosphor from Mitsubishi Chemical, Japan). In Fig. 4c we plot the quenching temperature  $T_{1/2}$  against the  ${}^4A_2 \rightarrow {}^4T_2$  energy for  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$ ,  $\text{K}_2\text{SiF}_6:\text{Mn}^{4+}$  and many other  $\text{Mn}^{4+}$ -doped fluoride phosphors reported in the literature (displayed data also listed in Table 1). The data show that the  $T_{1/2}$  increases with the energy of the  ${}^4T_2$  state. The clear trend shows that the thermal quenching in  $\text{Mn}^{4+}$ -doped fluorides is due to thermally activated crossover from the  ${}^4T_2$  excited state to the  ${}^4A_2$  ground state. Further confirmation for this quenching mechanism is provided by  $\text{Mn}^{4+}$  spectra measured at elevated temperatures (see Supplementary Information). Supplementary Figure S7 shows emission spectra of  $\text{K}_2\text{SiF}_6:\text{Mn}^{4+}$  at  $T = 573$  and  $673$  K. At  $573$  K a broad  ${}^4T_2 \rightarrow {}^4A_2$  emission band is observed, which is almost completely quenched at  $673$  K. The initial rise of the  ${}^4T_2 \rightarrow {}^4A_2$  emission at elevated temperatures confirms thermal population of the  ${}^4T_2$  level, which eventually leads to thermal quenching of all  $\text{Mn}^{4+}$  emission via this state.

To investigate whether thermally activated crossing via the  ${}^4T_2$  state is also responsible for temperature quenching in  $\text{Mn}^{4+}$ -doped oxides, we extend the data set of Fig. 4c with quenching temperatures reported for  $\text{Mn}^{4+}$ -doped oxides. Figure 4d shows the quenching temperature  $T_{1/2}$  as a function of the  ${}^4A_2 \rightarrow {}^4T_2$  energy for the  $\text{Mn}^{4+}$ -doped fluorides and oxides listed in Tables 1 and 2. The results show that  $T_{1/2}$  increases with the energy of the  ${}^4A_2 \rightarrow {}^4T_2$  transition. This indicates that the  $\text{Mn}^{4+}$  emission in fluorides and oxides are both quenched due to thermally activated crossover from the  ${}^4T_2$  excited state, and not the CT state as previously suggested in some reports<sup>24–27</sup>. The present results and analysis provide strong evidence that in many  $\text{Mn}^{4+}$  phosphors the thermal quenching mechanism involves thermally activated crossover via the  ${}^4T_2$  excited state. A contribution from other mechanisms cannot be ruled out and further research, for example, photoconductivity measurements and high pressure studies, can give additional information on the role of alternative quenching mechanisms.

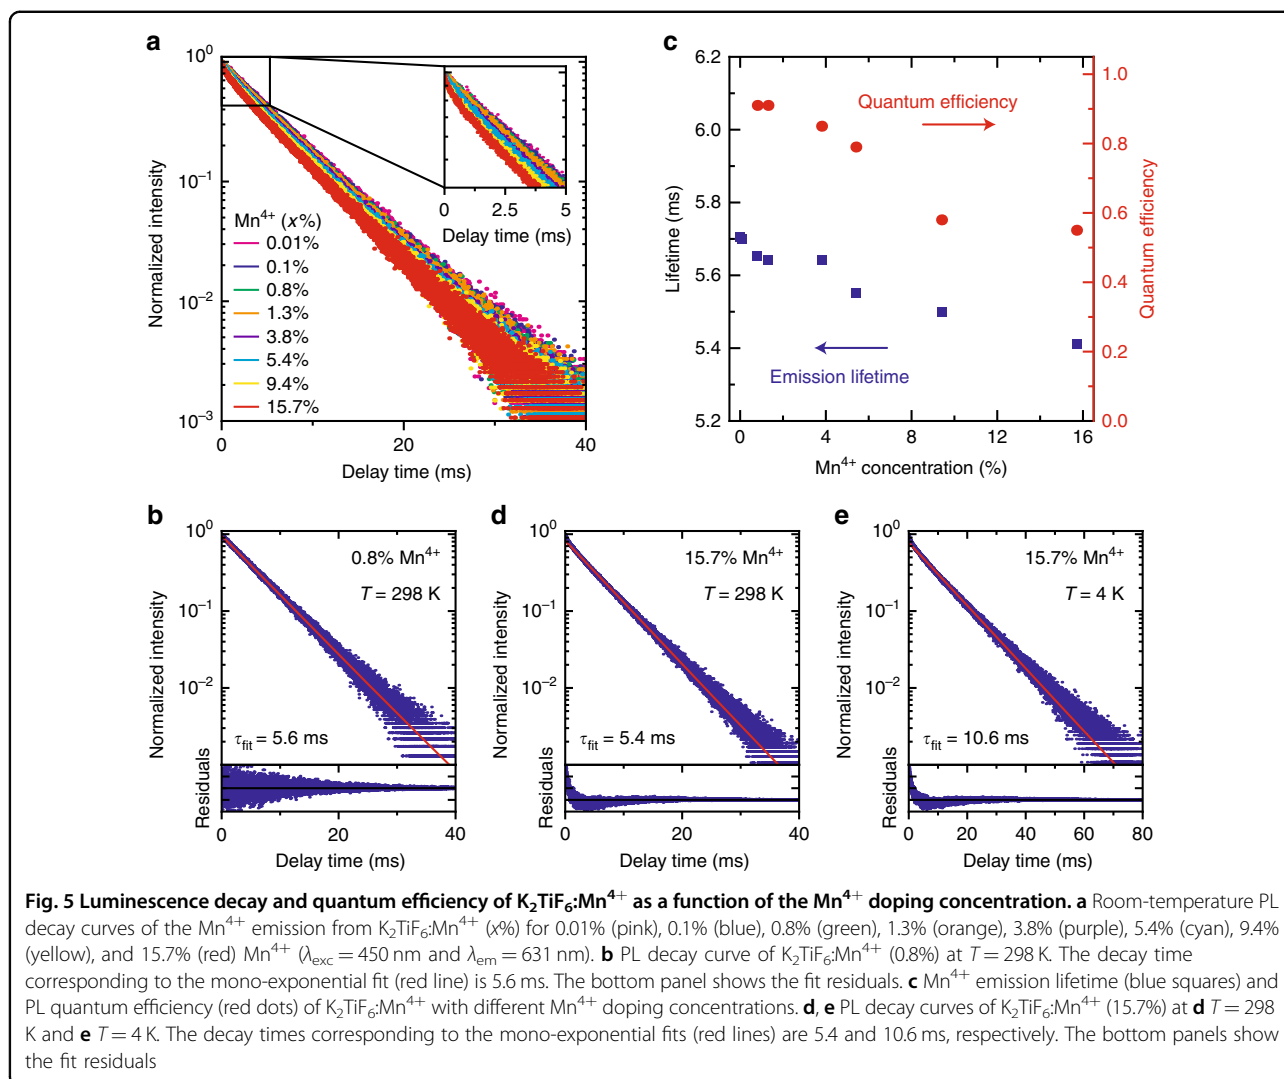

As quenching occurs by thermally activated crossover via the  ${}^4\text{T}_2$  excited state, the quenching temperature  $T_{1/2}$  of the  $\text{Mn}^{4+}$  luminescence is controlled by the energy of the  $\text{Mn}^{4+}$   ${}^4\text{T}_2$  state (the dependence of  $T_{1/2}$  on the energy of the  ${}^4\text{T}_2$  state is shown in Fig. 4c,d). In addition, the  $T_{1/2}$  of the  $\text{Mn}^{4+}$  luminescence depends on the offset  $\Delta R$  between the  ${}^4\text{T}_2$  and  ${}^4\text{A}_2$  states, as  $\Delta R$  also determines where the  ${}^4\text{T}_2$  and  ${}^4\text{A}_2$  states cross in the configuration coordinate diagram (Fig. 4a,b). The horizontal displacement of the  ${}^4\text{T}_2$  parabola will influence the quenching temperature. A variation in  $\Delta R$  can explain the spread observed in the data of Fig. 4c and d. To investigate the variation in the offset  $\Delta R$  for  $\text{Mn}^{4+}$ -doped fluorides, we compare the bandwidth of the  ${}^4\text{A}_2 \rightarrow {}^4\text{T}_2$  excitation band in  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$ ,  $\text{K}_2\text{SiF}_6:\text{Mn}^{4+}$  and  $\text{Cs}_2\text{HfF}_6:\text{Mn}^{4+}$  (see Supplementary Figure S9). The width of the  ${}^4\text{A}_2 \rightarrow {}^4\text{T}_2$  excitation band is controlled by the displacement of the  ${}^4\text{T}_2$  state and therefore gives a good indication of  $\Delta R$ . Comparison of the  ${}^4\text{A}_2 \rightarrow {}^4\text{T}_2$  bandwidths shows

that there is a variation in  $\Delta R$  for  $\text{Mn}^{4+}$ -doped fluorides. The variation in  $\Delta R$  is small, however, compared to the differences in the  ${}^4\text{T}_2$  energy, and no correlation is observed between the spectral width and quenching temperatures. This indicates that the  ${}^4\text{T}_2$  level energy has the largest influence on the quenching temperature of  $\text{Mn}^{4+}$ -doped fluorides.

Finally, in view of applications, it is interesting to see how we can control the  ${}^4\text{T}_2$  level energy (and thereby  $T_{1/2}$ ) through the choice of the host lattice. The energy of the  $\text{Mn}^{4+}$   ${}^4\text{T}_2$  state depends on the crystal field splitting  $\Delta_{\text{O}}$  (Fig. 2b), where  $\Delta_{\text{O}}$  is typically larger for shorter Mn–F distances<sup>44,58</sup>. For  $\text{Mn}^{4+}$ -doped fluorides the luminescence quenching temperature can therefore be raised by selecting host lattices with short  $\text{M}^{4+}$ – $\text{F}^-$  distances (see Supplementary Figure S10a). This is consistent with findings that  $T_{1/2}$  increases if the radius of the  $\text{M}^{4+}$  host cation decreases, as expected based on crystal field theory<sup>11,18</sup>. If, however,  $T_{1/2}$  is plotted against the  $\text{M}^{4+}$ -ligand

distance for both  $\text{Mn}^{4+}$ -doped fluorides and  $\text{Mn}^{4+}$ -doped oxides (see Supplementary Figure S10b), no correlation between  $T_{1/2}$  and the  $\text{M}^{4+}$ -ligand distance is found. This shows that the crystal field splitting and  ${}^4\text{T}_2$  energy give a better indication of the quenching temperature for  $\text{Mn}^{4+}$ -doped phosphors.

### Concentration quenching

In addition to insight into thermal quenching, concentration quenching in  $\text{Mn}^{4+}$ -doped fluorides is important for application in w-LEDs. The weak parity-forbidden  ${}^4\text{A}_2 \rightarrow {}^4\text{T}_2$  absorption requires that commercial phosphors have high  $\text{Mn}^{4+}$  concentrations. If there is effective concentration quenching, the PL decay time and QE will decrease when the  $\text{Mn}^{4+}$  doping concentration is raised<sup>26,28</sup>. We therefore investigate concentration quenching in  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$  by measuring the PL decay times and QEs of  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$  phosphors with  $\text{Mn}^{4+}$  concentrations ranging from 0.01 to 15.7%  $\text{Mn}^{4+}$ .

Figure 5a presents room-temperature PL decay curves of the  $\text{Mn}^{4+}$  emission from  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$  with increasing  $\text{Mn}^{4+}$  doping concentration  $x$ . It can be seen that the PL decay becomes slightly faster as the  $\text{Mn}^{4+}$  concentration increases. We analyze the decay dynamics by single exponential fitting of the PL decay curves. The fit for  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$  (0.8%) is shown in Fig. 5b. The fit residuals (bottom panel) are random and the PL decay thus resembles a single exponential. This indicates that the decay of the  ${}^2\text{E}$  state is mainly radiative. Consequently, the  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$  (0.8%) phosphor has a very high QE of 90%. Figure 5c gives an overview of the fitted decay times (blue squares) and QEs (red dots) of  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$  with different  $\text{Mn}^{4+}$  concentrations. The emission lifetime barely shortens if the  $\text{Mn}^{4+}$  concentration is increased (5.7 ms for 0.01%  $\text{Mn}^{4+}$  to 5.4 ms for 15.7%  $\text{Mn}^{4+}$ ). This suggests that energy migration to quenching sites is inefficient in  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$ . To verify this, we look at the QE values obtained for the  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$  ( $x\%$ ) phosphors. The QE remains above 80% for  $\text{Mn}^{4+}$  doping concentrations of 5% or less, which shows that concentration quenching is indeed limited up to a concentration of 5%  $\text{Mn}^{4+}$  ions. This result is important for applications in w-LEDs, as these high  $\text{Mn}^{4+}$  doping concentrations (e.g., 5 mol%) are required for sufficient absorption of the blue LED light in the parity-forbidden  $d-d$  transitions<sup>12</sup>.

For higher  $\text{Mn}^{4+}$  concentrations ( $x > 10\%$ ), non-radiative decay from the  ${}^2\text{E}$  excited state becomes stronger, however, and as a result the QE of  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$  falls below 60% (Fig. 5c). The non-radiative decay is also visible in the PL decay curve of  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$  (15.7%), shown in Fig. 5d. The decay is multi-exponential, which proves that with 15.7%  $\text{Mn}^{4+}$  the  ${}^2\text{E}$  state decays both radiatively and non-radiatively. The faster initial decay indicates that there is enhanced quenching by single-step energy

transfer for  $\text{Mn}^{4+}$  ions close to a quencher. In case of energy migration, a faster decay is also expected for longer times after the excitation pulse. As this is not observed, the contribution of energy migration via many  $\text{Mn}^{4+}$  ions to quenching sites seems to be small.

To further investigate the role of energy migration in the concentration quenching of the  $\text{Mn}^{4+}$  emission, we measure a PL decay curve of  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$  (15.7%) at  $T = 4\text{ K}$ , which is displayed in Fig. 5e. At  $T = 4\text{ K}$  energy migration among the  $\text{Mn}^{4+}$  ions (blue arrows in Fig. 1) will be hampered, as there is almost no spectral overlap between the  $\text{Mn}^{4+}$   ${}^2\text{E} \rightarrow {}^4\text{A}_2$  emission and  ${}^4\text{A}_2 \rightarrow {}^2\text{E}$  excitation lines (see Supplementary Figure S11). Hence, at 4 K non-radiative decay due to energy migration to quenching sites will be suppressed. The  $\text{Mn}^{4+}$  decay dynamics in Fig. 5e, however, show that the non-radiative decay is not suppressed at 4 K. The deviation from single exponential behavior is similar to that at 300 K. There is an initial faster decay (single-step energy transfer to quenching sites) followed by an exponential decay with a decay time very close to that measured for  $\text{Mn}^{4+}$  at low doping concentrations. This suggests that the decrease in QE at higher  $\text{Mn}^{4+}$  concentrations is not due to energy migration. The absence of strong concentration quenching by energy migration is confirmed by the thermal quenching behavior measured for the different  $\text{Mn}^{4+}$  concentrations. In Supplementary Figure S4, it can be seen that the luminescence quenching temperature is approximately the same for doping concentrations of 0.01% and 15.7%  $\text{Mn}^{4+}$ , which shows that effects due to thermally activated energy migration (i.e., concentration quenching) are weak. Hence, we conclude that the non-radiative decay at high  $\text{Mn}^{4+}$  concentrations is not caused by energy migration. Inefficient energy migration can be understood based on the strongly forbidden character of the  ${}^2\text{E} \rightarrow {}^4\text{A}_2$  transition. This allows only  $\text{Mn}^{4+}$ - $\text{Mn}^{4+}$  energy transfer via short range exchange interaction (see Supplementary Information for details).

We instead assign the non-radiative decay to direct transfer of excitation energy from  $\text{Mn}^{4+}$  ions to quenchers (green arrow in Fig. 1). This process can occur at all temperatures and becomes more efficient at higher  $\text{Mn}^{4+}$  dopant concentrations. With an increasing  $\text{Mn}^{4+}$  dopant concentration, the stress on the  $\text{K}_2\text{TiF}_6$  lattice grows and as a result more crystal defects (i.e., quenchers) may be formed. In addition, Mn in different valence states ( $\text{Mn}^{2+}$  and  $\text{Mn}^{3+}$ ) may be incorporated at higher  $\text{Mn}^{4+}$  concentrations. Even if a very small fraction of  $\text{Mn}^{4+}$  ions has a different valence state than 4+, effective quenching can occur via metal-to-metal charge-transfer states or direct energy transfer. Consequently, the probability for energy transfer to quenchers increases, resulting in faster initial PL decay and lower QEs for  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$  at high  $\text{Mn}^{4+}$  dopant concentrations. Optimized synthesis procedures

to reduce quenchers (defects and impurity ions) are thus crucial for obtaining highly luminescent  $\text{Mn}^{4+}$ -doped fluoride phosphors (see also recent work of Garcia-Santamaria et al.<sup>59</sup> on concentration quenching in  $\text{K}_2\text{SiF}_6:\text{Mn}^{4+}$ ).

## Conclusions

Narrow-band red-emitting  $\text{Mn}^{4+}$  phosphors form an important new class of materials for LED lighting and displays. For these applications, it is important to understand and control the luminescence efficiency. We have therefore investigated quenching of the  $\text{Mn}^{4+}$  luminescence in  $\text{Mn}^{4+}$ -doped fluorides by measuring the PL intensity and luminescence lifetimes of  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$  between 4 and 600 K and for  $\text{Mn}^{4+}$  concentrations from 0.01 to 15.7%. Temperature-dependent measurements of the  $\text{Mn}^{4+}$  emission intensity and lifetime for  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$  and other  $\text{Mn}^{4+}$ -doped phosphors show that thermal quenching is caused by thermally activated crossover via the  $\text{Mn}^{4+} \ ^4\text{T}_2$  excited state. As a result, the quenching temperature is higher in  $\text{Mn}^{4+}$ -doped materials with higher  $\ ^4\text{T}_2$  state energies. These findings can be used to engineer  $\text{Mn}^{4+}$ -doped fluoride phosphors with higher quenching temperatures for application in high-power w-LEDs.

Furthermore, quantum efficiency and luminescence decay measurements for a wide range of  $\text{Mn}^{4+}$  doping concentrations show that no concentration quenching occurs up to 5%  $\text{Mn}^{4+}$  in  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$ . This is important for the application of  $\text{Mn}^{4+}$ -doped materials in w-LEDs, as high  $\text{Mn}^{4+}$  doping concentrations (e.g., 5 mol%) are required for sufficient absorption of the blue LED light in the parity-forbidden  $\text{Mn}^{4+} \ d-d$  transitions. At very high  $\text{Mn}^{4+}$  doping concentrations (>10 mol%) the quantum efficiency of  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$  decreases due to enhanced direct energy transfer from  $\text{Mn}^{4+}$  to quenching sites. Concentration quenching by  $\text{Mn}^{4+}$ - $\text{Mn}^{4+}$  energy migration is limited. To optimize the efficiency in highly doped  $\text{Mn}^{4+}$  phosphors, a synthesis procedure aimed at reducing quenching sites (defects, impurity ions,  $\text{Mn}^{2+}$ , and  $\text{Mn}^{3+}$ ) will be crucial.

## Acknowledgements

We thank Stephan Zevenhuizen and Hans Meeldijk for performing the SEM and EDX measurements. Mart Peeters is acknowledged for measuring the PL quantum efficiencies. Suzanne Verkleij is acknowledged for taking the photographic images of the  $\text{K}_2\text{TiF}_6:\text{Mn}^{4+}$  phosphors. This work is financially supported by Technologiestichting STW, which is part of the Nederlandse Organisatie voor Wetenschappelijk Onderzoek (NWO).

## Author details

<sup>1</sup>Condensed Matter and Interfaces, Debye Institute for Nanomaterials Science, Utrecht University, P.O. Box 80000, 3508 TA Utrecht, The Netherlands. <sup>2</sup>Soft Condensed Matter, Debye Institute for Nanomaterials Science, Utrecht University, P.O. Box 80000, 3508 TA Utrecht, The Netherlands

## Conflict of interest

The authors declare that they have no conflict of interest.

**Supplementary information** is available for this paper at <https://doi.org/10.1038/s41377-018-0013-1>.

Received: 12 October 2017 Revised: 21 February 2018 Accepted: 7 March 2018 Accepted article preview online: 13 March 2018

Published online: 23 May 2018

## References

1. The Economist. Charge of the LED brigade: a global switch to LEDs will change the lighting business. 20 Aug (2011).
2. Krames, M. R. et al. Status and future of high-power light-emitting diodes for solid-state lighting. *J. Disp. Technol.* **3**, 160–175 (2007).
3. Harbers, G., Bierhuizen, S. J. & Krames, M. R. Performance of high power light emitting diodes in display illumination applications. *J. Disp. Technol.* **3**, 98–109 (2007).
4. Setlur, A. A. Phosphors for LED-based solid-state lighting. *Electrochem. Soc. Interface* **18**, 32–36 (2009).
5. Smet, P. F., Parmentier, A. B. & Poelman, D. Selecting conversion phosphors for white light-emitting diodes. *J. Electrochem. Soc.* **158**, R37–R54 (2011).
6. Bachmann, V., Ronda, C. & Meijerink, A. Temperature quenching of yellow  $\text{Ce}^{3+}$  luminescence in YAG:Ce. *Chem. Mater.* **21**, 2077–2084 (2009).
7. Ye, S., Xiao, F., Pan, Y. X., Ma, Y. Y. & Zhang, Q. Y. Phosphors in phosphor-converted white light-emitting diodes: recent advances in materials, techniques and properties. *Mater. Sci. Eng. R. Rep.* **71**, 1–34 (2010).
8. Xie, R. J. & Hirotsaki, N. Silicon-based oxynitride and nitride phosphors for white LEDs—a review. *Sci. Technol. Adv. Mater.* **8**, 588–600 (2007).
9. Setlur, A. A. et al. Energy-efficient, high color-rendering LED lamps using oxfluoride and fluoride phosphors. *Chem. Mater.* **22**, 4076–4082 (2010).
10. Lin, C. C., Meijerink, A. & Liu, R. S. Critical red components for next-generation white LEDs. *J. Phys. Chem. Lett.* **7**, 495–503 (2016).
11. Nguyen, H. D. & Liu, R. S. Narrow-band red-emitting  $\text{Mn}^{4+}$ -doped hexafluoride phosphors: synthesis, optoelectronic properties, and applications in white light-emitting diodes. *J. Mater. Chem. C* **4**, 10759–10775 (2016).
12. Radkov, E. V., Grigorov, L. S., Setlur, A. A., & Srivastava, A. M. Red line emitting phosphor materials for use in LED applications: US 749793B2. 2009-03-03.
13. Zhu, H. et al. Highly efficient non-rare-earth red emitting phosphor for warm white light-emitting diodes. *Nat. Commun.* **5**, 4312 (2014).
14. McKittrick, J. & Shea-Rohwer, L. E. Review: down conversion materials for solid-state lighting. *J. Am. Ceram. Soc.* **97**, 1327–1352 (2014).
15. Paulusz, A. G. Efficient Mn(IV) emission in fluorine coordination. *J. Electrochem. Soc.* **120**, 942–947 (1973).
16. Takahashi, T. & Adachi, S.  $\text{Mn}^{4+}$ -activated red photoluminescence in  $\text{K}_2\text{SiF}_6$  phosphor. *J. Electrochem. Soc.* **155**, E183–E188 (2008).
17. Wei, L. L. et al. A low-temperature co-precipitation approach to synthesize fluoride phosphors  $\text{K}_2\text{MF}_6:\text{Mn}^{4+}$  (M = Ge, Si) for white LED applications. *J. Mater. Chem. C* **3**, 1655–1660 (2015).
18. Sakurai, S., Nakamura, T. & Adachi, S.  $\text{Rb}_2\text{SiF}_6:\text{Mn}^{4+}$  and  $\text{Rb}_2\text{TiF}_6:\text{Mn}^{4+}$  red-emitting phosphors. *ECS J. Solid State Sci. Technol.* **5**, R206–R210 (2016).
19. Sijbom, H. F., Joos, J. J., Martin, I. I. D. J., Van den Eeckhout, K. & Poelman, D. et al. Luminescent behavior of the  $\text{K}_2\text{SiF}_6:\text{Mn}^{4+}$  red phosphor at high fluxes and at the microscopic level. *ECS J. Solid State Sci. Technol.* **5**, R3040–R3048 (2016).
20. Kasa, R. & Adachi, S. Red and deep red emissions from cubic  $\text{K}_2\text{SiF}_6:\text{Mn}^{4+}$  and hexagonal  $\text{K}_2\text{MnF}_6$  synthesized in  $\text{HF}/\text{KMnO}_4/\text{KHF}_2/\text{Si}$  solutions. *J. Electrochem. Soc.* **159**, J89–J95 (2012).
21. Nguyen, H. D., Lin, C. C., Fang, M. H. & Liu, R. S. Synthesis of  $\text{Na}_2\text{SiF}_6:\text{Mn}^{4+}$  red phosphors for white LED applications by co-precipitation. *J. Mater. Chem. C* **2**, 10268–10272 (2014).
22. Arai, Y. & Adachi, S. Optical transitions and internal vibronic frequencies of  $\text{MnF}_6^{2-}$  ions in  $\text{Cs}_2\text{SiF}_6$  and  $\text{Cs}_2\text{GeF}_6$  red phosphors. *J. Electrochem. Soc.* **158**, J179–J183 (2011).
23. Sekiguchi, D., Nara, J. & Adachi, S. Photoluminescence and Raman scattering spectroscopies of  $\text{BaSiF}_6:\text{Mn}^{4+}$  red phosphor. *J. Appl. Phys.* **113**, 183516 (2013).
24. Dorenbos, P. Charge transfer bands in optical materials and related defect level location. *Opt. Mater.* **69**, 8–22 (2017).
25. Blasse, G. & de Korte, P. H. M. The luminescence of tetravalent manganese in  $\text{CaZrO}_3:\text{Mn}$ . *J. Inorg. Nucl. Chem.* **43**, 1505–1506 (1981).

26. Blasse, G. & Grabmaier, B. C. *Luminescent Materials* (Springer-Verlag, Berlin, 1994).
27. Senden, T., Broers, F. T. H. & Meijerink, A. Comparative study of the  $Mn^{4+} {}^2E \rightarrow {}^4A_2$  luminescence in isostructural  $RE_2Sn_2O_7Mn^{4+}$  pyrochlores ( $RE^{3+} = Y^{3+}, Lu^{3+}$  or  $Gd^{3+}$ ). *Opt. Mater.* **60**, 431–437 (2016).
28. Dexter, D. L. & Schulman, J. H. Theory of concentration quenching in inorganic phosphors. *J. Chem. Phys.* **22**, 1063–1070 (1954).
29. Zhou, Q. et al.  $Mn^{4+}$ -activated  $BaSiF_6$  red phosphor: hydrothermal synthesis and dependence of its luminescent properties on reaction conditions. *Mater. Chem. Phys.* **170**, 32–37 (2016).
30. Jiang, X. et al. Hydrothermal synthesis and photoluminescence properties of red phosphor  $BaSiF_6Mn^{4+}$  for LED applications. *J. Mater. Chem. C* **2**, 2301–2306 (2014).
31. Lv, L., Jiang, X., Huang, S., Chen, X. & Pan, Y. The formation mechanism, improved photoluminescence and LED applications of red phosphor  $K_2SiF_6Mn^{4+}$ . *J. Mater. Chem. C* **2**, 3879–3884 (2014).
32. Zhong, J. et al. Synthesis and optical performance of a new red-emitting  $ZnTiF_6 \cdot 6H_2O Mn^{4+}$  phosphor for warm white-light-emitting diodes. *J. Alloy. Compd.* **662**, 232–239 (2016).
33. Xi, L. & Pan, Y. Tailored photoluminescence properties of a red phosphor  $BaSnF_6Mn^{4+}$  synthesized from Sn metal at room temperature and its formation mechanism. *Mater. Res. Bull.* **86**, 57–62 (2017).
34. Kim, M., Park, W. B., Bang, B., Kim, C. H. & Sohn, K. S. Radiative and non-radiative decay rate of  $K_2SiF_6Mn^{4+}$  phosphors. *J. Mater. Chem. C* **3**, 5484–5489 (2015).
35. Liao, J., Nie, L., Zhong, L., Gu, Q. & Wang, Q. Co-precipitation synthesis and luminescence properties of  $K_2TiF_6Mn^{4+}$  red phosphors for warm white light-emitting diodes. *Luminescence* **31**, 802–807 (2016).
36. Yeo, B. E., Cho, Y. S. & Huh, Y. D. Synthesis and photoluminescence properties of a red-emitting phosphor,  $K_2SiF_6Mn^{4+}$ , for use in three-band white LED applications. *Opt. Mater.* **51**, 50–55 (2016).
37. Bode, H., Jenssen, H. & Bandte, F. Über eine neue darstellung des kaliumhexafluoromanganats(IV). *Angew. Chem.* **65**, 304 (1953).
38. Roesky, H. W. *Efficient Preparations of Fluorine Compounds* (John Wiley & Sons, Inc, Hoboken, 2012).
39. Tanabe, Y. & Sugano, S. On the absorption spectra of complex ions. I. *J. Phys. Soc. Jpn.* **9**, 753–766 (1954).
40. Tanabe, Y. & Sugano, S. On the absorption spectra of complex ions II. *J. Phys. Soc. Jpn.* **9**, 766–779 (1954).
41. Henderson, B. & Imbusch, G. F. *Optical Spectroscopy of Inorganic Solids* (Oxford University Press, Oxford, 1989).
42. Ogjieglo, J. M. et al. Luminescence and luminescence quenching in  $Gd_3(GaAl)_5O_{12}$  scintillators doped with  $Ce^{3+}$ . *J. Phys. Chem. A* **117**, 2479–2484 (2013).
43. Bachmann, V., Jüstel, T., Meijerink, A., Ronda, C. & Schmidt, P. J. Luminescence properties of  $SrSi_2O_7$  doped with divalent rare earth ions. *J. Lumin.* **121**, 441–449 (2006).
44. Senden, T., van Harten, E. J. & Meijerink, A. Synthesis and narrow red luminescence of  $Cs_2HfF_6Mn^{4+}$ , a new phosphor for warm white LEDs. *J. Lumin.* **194**, 131–138 (2018).
45. Hoshino, R., Nakamura, T. & Adachi, S. Synthesis and photoluminescence properties of  $BaSnF_6Mn^{4+}$  red phosphor. *ECS J. Solid State Sci. Technol.* **5**, R37–R43 (2016).
46. Struck, C. W. & Fonger, W. H. Unified model of the temperature quenching of narrow-line and broad-band emissions. *J. Lumin.* **10**, 1–30 (1975).
47. Srivastava, A. M. et al. Unusual luminescence of octahedrally coordinated divalent europium ion in  $Cs_2M^{2+}P_2O_7$  ( $M^{2+} = Ca, Sr$ ). *J. Lumin.* **129**, 919–925 (2009).
48. Fonger, W. H. & Struck, C. W. Temperature dependences of  $Cr^{3+}$  radiative and nonradiative transitions in ruby and emerald. *Phys. Rev. B* **11**, 3251–3260 (1975).
49. de Jong, M., Seijo, L., Meijerink, A. & Rabouw, F. T. Resolving the ambiguity in the relation between Stokes shift and Huang–Rhys parameter. *Phys. Chem. Chem. Phys.* **17**, 16959–16969 (2015).
50. Dorenbos, P. Anomalous luminescence of  $Eu^{2+}$  and  $Yb^{2+}$  in inorganic compounds. *J. Phys. Condens Matter* **15**, 2645–2665 (2003).
51. Jin, Y. et al. Narrow red emission band fluoride phosphor  $KNaSiF_6Mn^{4+}$  for warm white light-emitting diodes. *ACS Appl. Mater. Interfaces* **8**, 11194–11203 (2016).
52. Brik, M. G. & Srivastava, A. M. Ab initio studies of the structural, electronic, and optical properties of  $K_2SiF_6$  single crystals at ambient and elevated hydrostatic pressure. *J. Electrochem. Soc.* **159**, J212–J216 (2012).
53. Zhdachevskii, Y. et al. Spectroscopic properties of  $Mn^{4+}$  ions in  $SrLaAlO_4$ . *Opt. Mater.* **35**, 1664–1668 (2013).
54. Geschwind, S., Kisliuk, P., Klein, M. P., Remeika, J. P. & Wood, D. L. Sharp-line fluorescence, electron paramagnetic resonance, and thermoluminescence of  $Mn^{4+}$  in  $\alpha-Al_2O_3$ . *Phys. Rev.* **126**, 1684–1686 (1962).
55. Thorington, L. Temperature dependence of the emission of an improved manganese-activated magnesium germanate phosphor. *J. Opt. Soc. Am.* **40**, 579–583 (1950).
56. Kemeny, G. & Haake, C. H. Activator center in magnesium fluorogermanate phosphors. *J. Chem. Phys.* **33**, 783–789 (1960).
57. Travníček, M., Kröger, F. A., Botden, T. P. J. & Zalm, P. The luminescence of basic magnesium arsenate activated by manganese. *Physica* **18**, 33–42 (1952).
58. Srivastava, A. M. & Brik, M. G. The dependence of 10 Dq crystal field parameter for  $Mn^{4+}$  ( $3d^3$  configuration) and the magnitude of  ${}^7F_1$  level splitting for  $Eu^{3+}$  ( $4f^6$  configuration) on pyrochlore compositions. *Opt. Mater.* **35**, 196–200 (2012).
59. Garcia-Santamaria, F., Murphy, J. E., Setlur, A. A. & Sista, S. P. Concentration quenching in  $K_2SiF_6Mn^{4+}$  phosphors. *ECS J. Solid State Sci. Technol.* **7**, R3030–R3033 (2018).
60. Wu, W. L. et al. High color rendering index of  $Rb_2GeF_6Mn^{4+}$  for light-emitting diodes. *Chem. Mater.* **29**, 935–939 (2017).
61. Mo, G. et al. Deep red  $BaTiF_6Mn^{4+}$  phosphor: synthesis, optical properties and application for warm WLED devices. *J. Mater. Sci. Mater. Electron* **28**, 8155–8159 (2017).
62. Li, P., Wondraczek, L., Peng, M. & Zhang, Q. Tuning  $Mn^{4+}$  red photoluminescence in  $(K,Rb)_2Ge_2O_7Mn^{4+}$  solid solutions by partial alkali substitution. *J. Am. Ceram. Soc.* **99**, 3376–3381 (2016).
63. Baur, F. & Jüstel, T. Dependence of the optical properties of  $Mn^{4+}$  activated  $A_2Ge_4O_9$  ( $A = K, Rb$ ) on temperature and chemical environment. *J. Lumin.* **177**, 354–360 (2016).
64. Jansen, T. et al. Narrow-band deep red photoluminescence of  $Y_2Mg_3Ge_3O_{12}: Mn^{4+}, Li^+$  inverse garnet for high power phosphor converted LEDs. *ECS J. Solid State Sci. Technol.* **7**, R3086–R3092 (2018).
65. Zhang, S. et al. Novel  $La_3GaGe_5O_{16}Mn^{4+}$  based deep red phosphor: a potential color converter for warm white light. *RSC Adv.* **5**, 90499–90507 (2015).
66. Takeda, Y., Kato, H., Kobayashi, M., Kobayashi, H. & Kakihana, M. Photoluminescence properties of  $Mn^{4+}$ -activated perovskite-type titanates,  $La_2M-TiO_6Mn^{4+}$  ( $M = Mg$  and  $Zn$ ). *Chem. Lett.* **44**, 1541–1543 (2015).
67. Chen, D., Zhou, Y. & Zhong, J. A review on  $Mn^{4+}$  activators in solids for warm white light-emitting diodes. *RSC Adv.* **6**, 86285–86296 (2016).
68. Riseberg, L. A. & Weber, M. J. Spectrum and anomalous temperature dependence of the  ${}^2E \rightarrow {}^4A_2$  emission of  $Y_3Al_5O_{12}Mn^{4+}$ . *Solid State Commun.* **9**, 791–794 (1971).
69. Peng, M., Yin, X., Tanner, P. A., Brik, M. G. & Li, P. Site occupancy preference, enhancement mechanism, and thermal resistance of  $Mn^{4+}$  red luminescence in  $Sr_4Al_{14}O_{25}Mn^{4+}$  for warm WLEDs. *Chem. Mater.* **27**, 2938–2945 (2015).
70. Da Fonseca, R. J. M. & Abritta, T. Radiative and nonradiative processes in  $LiGa_5O_8Mn^{4+}$ . *Phys. B Condens Matter* **190**, 327–332 (1993).