

Thermolysis-Driven Growth of Vanadium Oxide Nanostructures Revealed by *In Situ* Transmission Electron Microscopy: Implications for Battery Applications

Dnyaneshwar S. Gavhane, Atul D. Sontakke, and Marijn A. van Huis*

Cite This: *ACS Appl. Nano Mater.* 2023, 6, 7280–7289

Read Online

ACCESS |



Metrics & More




Article Recommendations



Supporting Information

ABSTRACT: Understanding the growth modes of 2D transition-metal oxides through direct observation is of vital importance to tailor these materials to desired structures. Here, we demonstrate thermolysis-driven growth of 2D V_2O_5 nanostructures via *in situ* transmission electron microscopy (TEM). Various growth stages in the formation of 2D V_2O_5 nanostructures through thermal decomposition of a single solid-state NH_4VO_3 precursor are unveiled during the *in situ* TEM heating. Growth of orthorhombic V_2O_5 2D nanosheets and 1D nanobelts is observed in real time. The associated temperature ranges in thermolysis-driven growth of V_2O_5 nanostructures are optimized through *in situ* and *ex situ* heating. Also, the phase transformation of V_2O_5 to VO_2 was revealed in real time by *in situ* TEM heating. The *in situ* thermolysis results were reproduced using *ex situ* heating, which offers opportunities for upscaling the growth of vanadium oxide-based materials. Our findings offer effective, general, and simple pathways to produce versatile 2D V_2O_5 nanostructures for a range of battery applications.

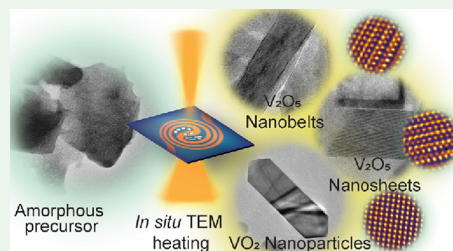

KEYWORDS: *in situ* transmission electron microscopy, thermolysis, 2D materials, V_2O_5 , VO_2 , *ex situ* growth

INTRODUCTION

Vanadium pentoxide (V_2O_5), the semiconductor in the transition-metal oxides family with a two-dimensional (2D)-layered structure, has attracted significant attention from the scientific community. Featuring high theoretical capacity, low cost, abundant source, good safety, and easy preparation methods, V_2O_5 has attracted enormous interest in rechargeable batteries.^{1–5} Because of the typical lamellar crystal structure of orthorhombic V_2O_5 , it has been extensively studied for application as a lithium-ion battery cathode material.^{6–8} Besides this, V_2O_5 has also attracted great attention as a potential candidate for catalysts⁹ and gas sensor applications.^{10–12}

Considering its exceptional and versatile role in various applications, a variety of synthesis methods to prepare V_2O_5 nanostructures has been developed including hydrothermal/solvothermal synthesis, sol–gel processing, template-based methods, electrochemical deposition, etc.¹³ Nanostructures of V_2O_5 consist of 1D nanorods,^{14,15} nanobelts,^{16,17} nanofibers,¹⁸ 2D nanosheets,^{19–23} 3D hollow porous,^{24,25} and hierarchical^{26,27} nanostructures. One-dimensional V_2O_5 nanostructures are prepared mostly with sol–gel and hydrothermal methods, which are relatively simple, using a V_2O_5 powder or V_2O_5 crystals as a precursor. Two-dimensional nanosheets are prepared with the liquid exfoliation of bulk V_2O_5 crystals²⁰ and the hydrothermal method.²⁸ All of these V_2O_5 nanostructures that are grown through different methods are continuously being used in rechargeable battery applications.


Thermolysis of ammonium metavanadate (AMV), an amorphous single solid-state precursor, produces crystalline V_2O_5 structures.^{29–32} Decomposing AMV precursor is a quite straightforward and feasible method to produce V_2O_5 nanostructures with no complex requirements or conditions. This unique and simple synthesis method has not been explored significantly compared to the conventional routes. An exploration of the underlying growth mechanisms of V_2O_5 nanostructures through the thermolysis of an amorphous single solid-state precursor provides an extraordinary opportunity to grow these nanostructures with great control. Real-time observations at the atomic scale of various physical and chemical processes of phase transitions,^{33–36} growth,^{37–39} and sublimation^{40–42} can be achieved by *in situ* transmission electron microscopy (TEM) with high spatial and temporal resolution. The *in situ* TEM technique has been extensively used to study the dynamic processes in various materials.^{34,43–49} *In situ* TEM growth of MoS_2 through thermolysis of a single solid-state precursor was observed in several experiments.^{50–52} In other experiments, 2D WS_2 vertical and horizontal layers were grown

Received: January 27, 2023

Revised: April 19, 2023

Accepted: April 20, 2023

Published: May 3, 2023



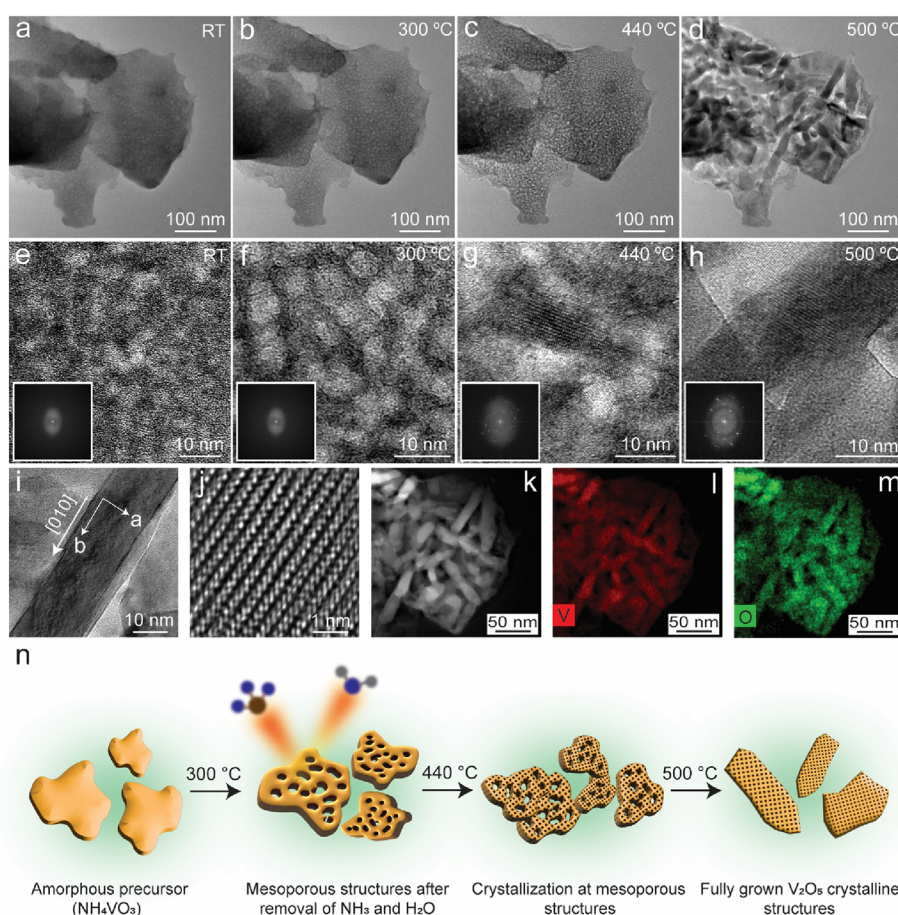


Figure 1. Growth of crystalline structures of V_2O_5 during *in situ* TEM heating of AMV precursor. (a–d) Low-magnification TEM images showing: (a) an amorphous AMV precursor at room temperature (RT) as drop cast onto the heating chip. (b) A mesoporous structure formed at 300 °C. (c) Evolution of crystalline structures on mesoporous structures at around 440 °C. (d) Fully grown crystalline V_2O_5 structures at 500 °C. (e–h) High-magnification TEM images showing: (e) AMV precursor at RT with a diffuse ring in the fast Fourier transform (FFT) in the inset. (f) Formation of holes in the precursor at 300 °C and a diffuse ring in the FFT in the inset. (g) Initiation of crystallization in the mesoporous structure at 440 °C, evident from the appearance of dots in the FFT in the inset. (h) One of the fully grown V_2O_5 structures with lattice fringes. The corresponding FFT in the inset shows an increased number of dots. (i) The TEM image of one of the V_2O_5 nanobelts (NB) grown out of AMV precursor. (j) The high-resolution TEM image of the nanobelt showing atomic columns. (k) The HAADF-STEM image of the V_2O_5 structures from panel d. (l, m) STEM-EDS elemental maps for vanadium (V) and oxygen (O) in V_2O_5 structures. (n) Scheme presenting the overall process of thermal decomposition of AMV precursor to fully grown V_2O_5 structures with temperature.

in TEM through thermal decomposition of a single solid-state precursor.^{53,54} Metal oxide nanomaterials were also observed to grow during *in situ* TEM experiments.^{55–57}

In this work, with the combination of *in situ* TEM heating and thermolysis of ammonium metavanadate (NH_4VO_3) inside the TEM, we have observed the real-time growth of crystalline V_2O_5 nanostructures on the SiN_x membrane of the heating chip. The heating of the precursor inside the TEM shows multiple growth stages to finally yield the shape of crystalline V_2O_5 nanostructures. The formation of mesoporous structures on an amorphous precursor due to the removal of NH_3 and H_2O to the crystallization at a small scale was observed in real time during the thermolysis. Two different types of final nanostructures are observed during this *in situ* TEM thermolysis process for the V_2O_5 ; 1D nanobelts and 2D nanosheets. The phase transformation of 2D V_2O_5 to 3D VO_2 nanostructures is also observed at elevated temperatures in the *in situ* TEM experiment. All these intermediate processes cannot be observed and controlled by means of conventional growth methods, while with *in situ* TEM, it is possible to observe these in real time and to gain control over the different growth stages of V_2O_5

nanostructures to obtain the desired materials. These *in situ* TEM results can be used to fine-tune the growth parameters during the thermolysis to design V_2O_5 nanomaterials, which are highly relevant for rechargeable battery applications.

EXPERIMENTAL SECTION

In Situ Transmission Electron Microscopy. *In situ* TEM heating experiments were performed on a DENSolutions heating holder and Wildfire S3 heating chip with electron transparent ~ 30 nm thick SiN_x windows. Before the *in situ* TEM heating, the samples were prepared by dissolving high purity NH_4VO_3 (AMV) (Sigma-Aldrich, 99.9%) in ethanol to form 5 vol % solutions. These solutions were sonicated for 15 min, drop cast onto the plasma cleaned heating chip, and dried in air. The heating chip was then introduced into an FEI Talos F200X TEM operated at 200 kV for imaging. In all the TEM heating experiments, samples were preheated to 100 °C for at least 10 min to remove organic residues. The temperature was then increased from 100 to 700 °C in steps of 20 °C. During *in situ* TEM heating, after each 100 °C, the temperature was held constant to observe and image growth changes in the first pilot experiment. The TEM heating experiments were repeated multiple times. Scanning TEM (STEM) imaging on the FEI Talos F200X was conducted using a probe current of 30 pA and a dwell time

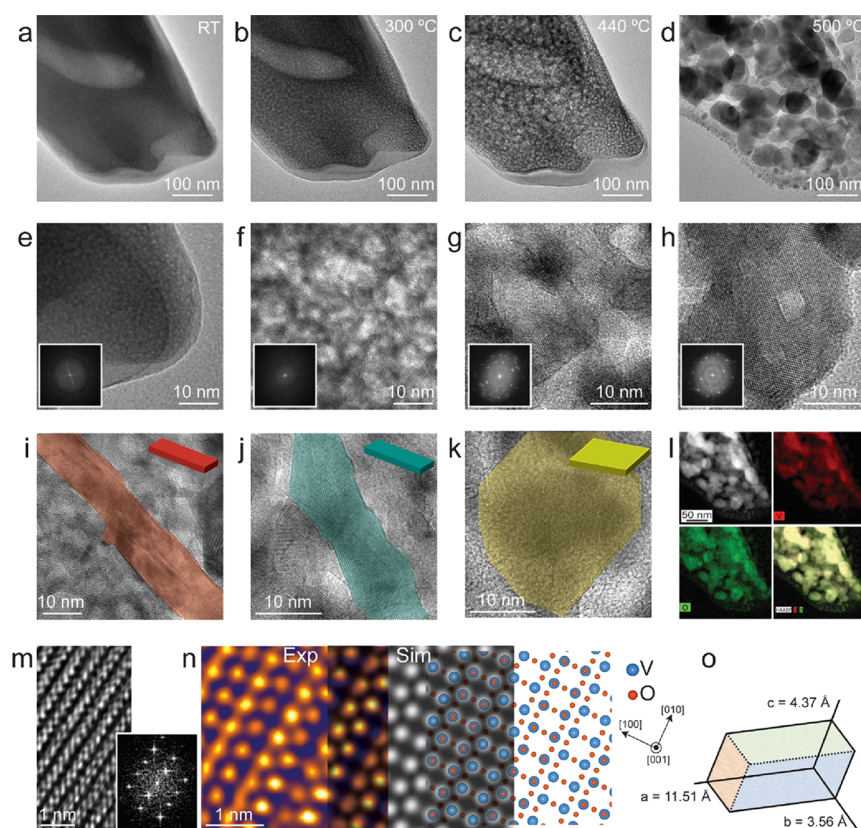



Figure 2. *In situ* growth of distinct V_2O_5 structures. (a–d) TEM images were captured at: (a) room temperature with an amorphous AMV precursor, (b) 300 °C with a mesoporous amorphous precursor, (c) 440 °C with initialization of crystallization of V_2O_5 , and (d) 500 °C with fully grown structures of V_2O_5 . (e–h) Magnified TEM images along with the corresponding FFTs in the inset for panels a–d, respectively. (i, j) Few-layered nanobelt structures of V_2O_5 with growth dominant along one direction. (k) Growth in two directions of the nanosheet (NS)-like structures of V_2O_5 . The colors overlaid on the structures are used to emphasize the observed 1D NB and 2D NS structures. (l) The HAADF-STEM image and EDS maps for V and O along with the altogether overlaid image from the area shown in panel d. (m) The spatially resolved HRTEM image from one of the fully grown V_2O_5 structures shown in panel h along with the corresponding FFT. (n) Combination of overlapped experimental, simulated HRTEM images, and an atomic model for orthorhombic V_2O_5 projected along the (001) direction (the TEM image was processed with the GEM LUT effect in ImageJ software for better visualization). The blue and red balls represent vanadium (V) and oxygen (O) atoms, respectively. The orthographic projection shows the viewed direction. (o) The sketch of an orthorhombic unit cell of V_2O_5 .

per pixel of 4.0 μs . All EDS chemical mapping experiments were performed on the Talos F200X TEM equipped with a Chemi-STEM elemental analysis setup. Each of the EDS maps was recorded for 15 min to improve the signal-to-noise ratio. The stoichiometry of the vanadium oxides was determined by EDS quantification, using a standard software package supplied with a TalosF200X microscope (TFS software). The Cliff-Lorimer method was used for EDS quantification. The spatial resolution of the *in situ* set-up is 1.2 Å (the resolution of the TalosF200X microscope is not degraded at elevated temperature), while the temporal resolution both in TEM and STEM corresponds to a recording rate of 20 frames per second or higher. For all the filtered images, the contrast was improved between the material and amorphous region in the background by applying a mask on the amorphous region followed by the inverse fast Fourier transformation (IFFT) for better display purposes. The TEM imaging simulations were performed using QSTEM software. The simulated image was generated with the following settings: accelerating voltage: 200 kV, objective aperture: 15 mrad, convergence angle: 1 mrad, focal spread: 2 nm, defocus: 10.

Ex Situ Experiments and Characterization. The *ex situ* heating experiments were performed in a vacuum oven Nabertherm RHTH tube oven with a maximum of 1800 °C heating capacity at 2 mbar pressure. All the *ex situ* experiments reported in this article were performed at 400 and 450 °C for 10 min, after carrying out a few pilot experiments at 350, 400, and 500 °C to optimize the growth temperature. The samples for *ex situ* vacuum oven growth were prepared similarly as they were made for *in situ* TEM heating.

RESULTS AND DISCUSSION

Thermal Decomposition of Ammonium Metavanadate. A single solid-state precursor, ammonium metavanadate (NH_4VO_3 , abbreviated as AMV), was heated in the *in situ* TEM experiments to observe and investigate the growth of crystalline vanadium oxide structures, V_2O_5 and VO_2 , using a dedicated *in situ* heating holder. The previous research reported on the thermal decomposition of AMV in different gaseous environments (vacuum, argon, nitrogen, and air) to produce V_2O_5 , which can be shown with the following simple equation:^{29–32}



The reaction is much more complicated than shown in the above equation where different intermediate products at intermediate temperatures can be obtained, but these are mostly very poorly crystalline or even amorphous.^{29–32} This suggests that thermal decomposition of the AMV precursor leads to the growth of the only pure crystalline structure, V_2O_5 . This is one of the easiest and less complex methods to grow crystalline V_2O_5 structures, which can be used for various applications. Apart from one of the *in situ* TEM experiments where amorphous V_2O_5 was transferred to crystalline orthorhombic V_2O_5 ,⁵⁸ not

many attempts were made to observe the growth of vanadium oxide-based materials via *in situ* TEM. The V_2O_5 nanobelts⁵⁹ and nanosheets^{28,60,61} prepared with this method of thermal decomposition of AMV precursor show to be an excellent candidate as a cathode for Li-ion battery applications in comparison to the conventionally grown nanobelts and nanosheets using amorphous or crystal V_2O_5 precursors.^{17,19,20,62,63} Although precise control over the thickness and growth of the nanobelts or nanosheets is not a strong feature of this method, it provides a great opportunity to observe and investigate the growth of V_2O_5 -based structures through *in situ* TEM experiments with no requirements of specialized instruments. Besides this, the synthesis route can be likely scaled up and fine-tuned with the help of the *in situ* TEM findings.

***In Situ* TEM Growth of V_2O_5 Nanostructures.** An AMV precursor in ethanol solution was drop cast onto the ~ 30 nm thick SiN_x membrane of a TEM heating chip and dried in air to prepare samples for *in situ* TEM experiments. With the help of a controlled heating setup, the prepared heating chip was introduced into the TEM column. The schematics in Figure S1 depict the whole scenario of preparing a heating chip for the *in situ* TEM experiments. To remove any residues present in the solvent on the heating chip, it was heated from room temperature to 100 °C for ~ 10 min (see Figure S2 and Supporting Note 1 in the Supporting Information for more details). The temperature was then increased to 700 °C in steps of 20 °C withholding the temperature at different stages for a few minutes to monitor and capture the frames of the changes in the precursor.

A brief story of the growth of crystalline V_2O_5 structures through thermal decomposition of a single, solid-state, and amorphous AMV precursor with *in situ* TEM heating is shown in Figure 1. The amorphous AMV precursor at room temperature (RT) in TEM gives an image as shown in Figure 1a. Figure 1e shows a close-up look at the amorphous AMV precursor along with the diffuse ring in the fast Fourier transform (FFT) shown in the inset, from which it is evident that the precursor is amorphous prior to any heat treatment. With the temperature reaching 300 °C in Figure 1b, the amorphous precursor starts to form a mesoporous structure by forming holes that are clearer in Figure 1f and the structure remains amorphous as is evident from the absence of any bright dots in the FFT in the inset in Figure 1f. The first appearance of the crystalline structures on the mesoporous amorphous structure was captured at a temperature of 440 °C. The high-magnification TEM image along with the presence of dots in the FFT in the inset in Figure 1g manifests the amorphous-to-crystalline transition at 440 °C. Figure 1d shows the emergence of well-defined shapes of nanobelts (NBs) of crystalline V_2O_5 , which becomes clearer in Figure 1h and with the larger number of bright spots in FFT in the inset. The V_2O_5 NBs are seen to be grown along the *b* axis as shown in Figure 1i. A close inspection at the edges of the V_2O_5 NB in Figure 1i suggests that it has a multilayer configuration, which is typical of the structure of an NB. Figure 1j shows the high-resolution TEM (HRTEM) image from the part of the V_2O_5 NB in Figure 1i. This shows the typical arrangements of atomic lattices in orthorhombic V_2O_5 structures.

A slightly zoomed-in HAADF-STEM image of the grown V_2O_5 structures at 500 °C, along with the STEM-EDS maps for vanadium and oxygen, is shown in Figure 1k–m, respectively. The schematic in Figure 1n represents the overall process of the growth of crystalline V_2O_5 structures from amorphous precursor with increasing temperatures. The mesoporous structure forms

after heating the precursor to 300 °C after the removal of NH_3 and H_2O as mentioned in eq 1. This becomes clearer once the crystallization of V_2O_5 starts after heating to 440 °C as evidenced by the difference in contrast as seen in Figure 1c. Increasing the temperature further to 500 °C forms fully grown, nicely defined, and crystallized V_2O_5 structures.

The *in situ* TEM observations suggest that there are different types in the final morphology of the V_2O_5 structures, which can be subdivided into 1D NBs and 2D nanosheets (NSs). Figure 1 shows the dominant growth of few-layered 1D NBs of V_2O_5 , whereas Figure 2 shows the growth of V_2O_5 structures progressed along 2D, which are designated as NSs. Figure 2 shows the gradual growth of crystalline V_2O_5 structures in a completely independent experiment, at the same temperatures shown in Figure 1 but with a major difference in the final morphology. The blurred TEM image in Figure 2a at RT along with the corresponding FFT in the inset of Figure 2e confirms the amorphous nature of the AMV precursor. Figure 2b,f confirms the formation of the porous structure of the precursor at 300 °C after the removal of NH_3 and H_2O molecules as mentioned in an earlier section. Crystallization of V_2O_5 starts to occur at 440 °C, which is evident from the clear appearance of lattice fringes in Figure 2g and the increased number of bright spots in the FFT in the inset of Figure 2g, which gives the contrast difference in Figure 2c. Figure 2d shows fully grown crystalline V_2O_5 structures at 500 °C, which is different from the structures (NBs) seen in Figure 1d. One of the nicely crystalline structures is shown in Figure 2h, which gives an impression of a few-layered 2D nanosheet. Figure 2i,j shows an image of typical NBs observed at a different location on the heating chip at the temperature of 500 °C. The colors overlaid in Figure 2i,j on the V_2O_5 structures (red and dark cyan, respectively), along with the schematic models, suggest the one-directional growth of NBs, whereas the golden yellow color overlaid on the V_2O_5 structure, and the schematic model in Figure 2k, proposes the 2D growth of NSs. Figure 2l depicts the HAADF-STEM image and EDS maps for vanadium and oxygen for the same area as shown in Figure 2d, which also helps to confirm the observed structures of V_2O_5 . A typical atomic column image for orthorhombic V_2O_5 along with the FFT is shown in Figure 2m. A filtered TEM image of the atomic columns in V_2O_5 is matched with the simulated image and atomic model for orthorhombic V_2O_5 in Figure 2n. This suggests that the observed image is visualized along the *c* axis. Figure 2o shows the sketch of an orthorhombic unit cell of V_2O_5 . The highly resolved atomic column images of V_2O_5 are viewed through the *c* axis direction of the unit cell. Most of the NBs and NSs are oriented in the [001] zone axis, which is the basal plane, with a few of them oriented in other directions as well. However, we specifically choose to monitor those that are oriented in the [001] zone axis to obtain better images and hence obtain a better understanding of the crystal structure.

It was found that the electron beam did not have a significant influence on the observations, which became clear from reference measurements (see Supporting Note 2 and Supporting Figure S3): after keeping one of the precursor areas on the heating chip under the exposure of the electron beam at room temperature for more than 10 min, it did not lead to any significant changes in it, as evidenced by the absence of any visible lattice fringes in the TEM images in Figure S3a, b. A similar process of the thermal decomposition of AMV precursor as observed in the *in situ* heating with continuous exposure of precursor to the electron beam is observed when the precursor

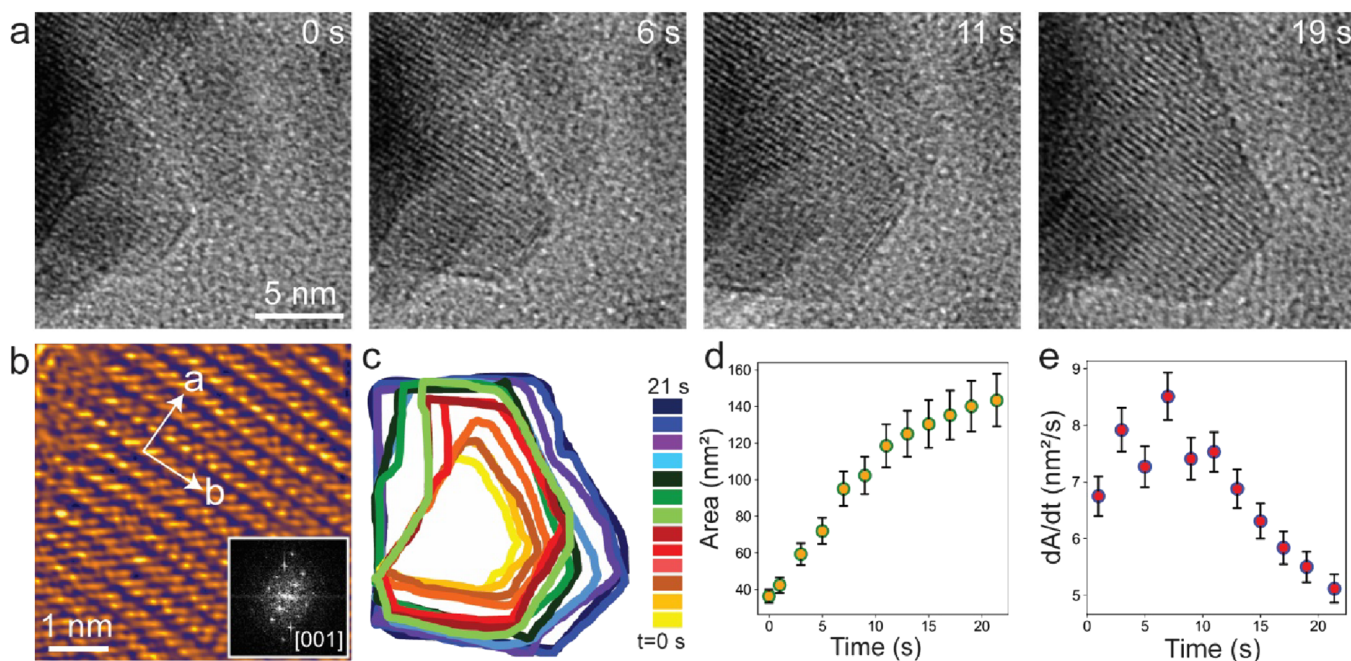


Figure 3. Real-time observation of growth of the V_2O_5 nanosheet. (a) Time-series frames at different growth stages. (b) The high-magnified filtered image from the grown V_2O_5 NS and FFT in the inset (the TEM image was processed with the GEM LUT effect in ImageJ software for better visualization). (c) Contour maps at different growth steps. (d, e) Plots of the increased area of NS with time and the growth rate at different times, respectively.

was kept away from the electron beam by blanking it during the entire period of heating (see Figure S3c–f and Supporting Note 2).

Several *in situ* TEM experiments were carried out in which both these structures of V_2O_5 (NBs and NSs) are observed on the same heating chip and at the same locations in mixed forms. This can be the result of multiple factors, out of which the thickness of the AMV precursor before heating could be one. In our previous work on WS_2 growth through thermolysis, we observed the selective growth of vertical and horizontal WS_2 flakes depending on the thickness of the precursor.⁵⁴ In the present study, however, controlling the thickness of AMV precursor was not a straightforward task, and besides that, both structures are observed to grow in a mixture without a clear clue on how to gain control over the one type of structure. This keeps an interesting question open for a further scientific explanation to obtain the desired type of growth of V_2O_5 through this clean method. Because of the random mixture of these morphologies, it is difficult to specify the distribution of them within the sample, but for all of the experiments, the appearance of growth of NBs and NSs is similar.

Real-time observations of the growth of nanostructured materials provide interesting and vital information with the help of which understanding of and control over the growth process can be gained much more efficiently.^{48,50–54,56} The time-series frames captured at different growth stages for V_2O_5 NSs are presented in Figure 3a. The movie (Supporting Movie 1) was recorded at the midway temperature of 460 °C after the crystalline V_2O_5 grows out of an amorphous precursor. Movie frames recorded after 0, 6, 11, and 19 s are displayed in Figure 3a and show the gradual in-plane growth of the NS in two directions. The zeroth second in the first frame in Figure 3a is indexed to show the beginning of the growth of NS, and the following times refer to the different growth stages. It can be seen from the frames in Figure 3a that the NS grows with sharp

edges and corners with good crystallinity. Figure 3b shows a filtered image from the last frame of the movie, which displays atomic columns in the orthorhombic V_2O_5 NS that is oriented horizontally parallel to the SiN_x membrane of the heating chip. In all of the *in situ* experiments, it has been observed that almost all of the V_2O_5 structures are lying flat on the SiN_x membrane with a c axis parallel to the viewing direction. This is evident from all of the figures (Figures 1, 2, and 3) discussed in earlier sections. The FFT in the inset of Figure 3b displays the single-crystalline nature of the grown orthorhombic V_2O_5 NS. The multicolored contour maps in Figure 3c showing the time evolution give an idea about the average growth of the V_2O_5 structures. This shows that, during the growth, the area of the NS initially increases fast, while it grows relatively slowly further on as shown in the plot in Figure 3d. The growth rate plot in Figure 3e shows that it increases sharply for a few seconds and then drops down gradually until the twentieth second when the NS does not show any further growth. This in turn explains the limited area growth of NBs and NSs displayed in Figures 1 and 2.

Movies of NB growth are not included as these were found to grow too fast after changing the temperature to the growth temperature. We attempted to capture the real-time growth process of NBs but these either grew fast with the growth temperature, or did not transform into a clear shape when continuously imaged with the electron beam. This could be the effect of the electron beam on the growth, an effect that was not observed during the growth of NSs. *In situ* movies of NB growth are therefore not included in order not to report results that may be the result of the electron beam effects.

Phase Transition of 2D V_2O_5 to 3D VO_2 Nanostructures. Obtaining two different materials of the same elements from one precursor can be an efficient way of synthesis. Phase transitions in materials provide the capability to produce two differently characterized materials that can be used in multiple applications individually. As discussed in earlier sections, the

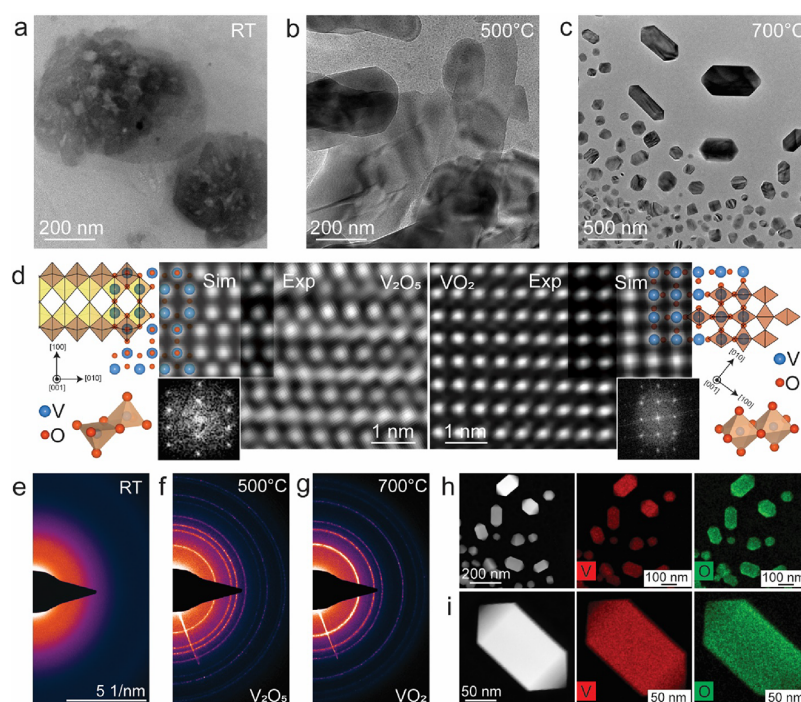


Figure 4. Phase transition in V_2O_5 . (a) An amorphous AMV precursor at RT. (b) A few layered crystalline V_2O_5 structures at 500 °C. (c) Nanostructures of VO_2 at 700 °C. (d) Combination of experimental TEM images mapped with simulated images and atomic models for both V_2O_5 and VO_2 along with the corresponding FFTs. The blue and red balls in both cases represent vanadium and oxygen atoms, respectively. (e–g) Electron diffraction patterns of AMV precursor, crystalline V_2O_5 , and VO_2 at the corresponding temperatures. (h) The HAADF-STEM image and EDS elemental maps for vanadium and oxygen of multiple and (i) single VO_2 structures after heating to 700 °C.

amorphous AMV precursor transforms into various crystalline V_2O_5 nanostructures. It has been observed previously that the V_2O_5 can be transformed into multiple phases of VO_x .^{64–67}

Figure 4a shows the amorphous AMV precursor at room temperature, which then transformed into the thin-crystalline V_2O_5 NBs and NSs at 500 °C as shown in Figure 4b. When increasing temperature further, the V_2O_5 nanostructures show good thermal stability until the temperature reaches 700 °C. At that temperature, the thin nanostructures of V_2O_5 collapse into sharp-edged three-dimensional nanoparticles, which is evident from their shape as displayed in Figure 4c. These nanoparticles show various shapes and sizes along with different thicknesses, but their three-dimensional and strongly faceted nature is a common factor, unlike thin V_2O_5 nanostructures. The crystallinity difference of the V_2O_5 nanostructures from the obtained nanoparticles is shown in Figure 4d with the help of filtered HR-TEM images, simulated images, schematics of atomic models, and FFTs. The EDS elemental maps in Figure 4h,i for vanadium and oxygen from a group of nanoparticles, and of the larger individual sharp-edged nanoparticle, show a 1:2 stoichiometry between V and O, which confirms the VO_2 composition. The process of the phase transition from V_2O_5 to VO_2 was so rapid that capturing it through TEM was impossible, which is why there are no videos capturing this. Increasing the temperature to 700 °C made the V_2O_5 structures transform no time into particles of VO_2 .

A detailed analysis of the atomically resolved images in Figure 4d of the three-dimensional nanoparticles gives interplanar distances of 0.45 nm, which represents the (010) plane for monoclinic, and (100) and (010) planes for rutile, phases of VO_2 .⁶⁸ The insulator-to-metal transition between the two phases of VO_2 occurs near room temperature in which the monoclinic phase is the low-temperature phase, while rutile is

the high-temperature phase.^{69,70} Thus, it suggests that the nanoparticles obtained after the phase transition from V_2O_5 at 700 °C show a rutile phase of VO_2 as it stays in this phase without showing any changes after heating to 740 °C. During the experiments, the monoclinic phase may have been formed as an intermediate phase as well while this was not recorded in the images as the temperature is quite high, or the rutile phase was formed directly not via the formation of the monoclinic phase. Increasing the temperature to 740 °C does not change the crystal structure, and this also suggests that the observed phase is rutile, which is stable at higher temperatures. As both these phases, monoclinic and rutile, have different properties (insulating and metallic), they have different applications based on their properties. In our experiments, we found that the rutile phase of VO_2 is stable at 740 °C, and therefore, it is possible to form this as a stable nanoscale phase under controlled experimental conditions. The VO_2 particles that converted from the NBs and NSs of V_2O_5 were found oriented in random directions as they can be seen in 3D shapes in contrast to the 2D NBs and NSs that were all found in (nearly) the same orientation. The temperature profile plot in Figure S2 shows the increased temperature from 700 to 760 °C with the same phase of VO_2 . In a separate experiment, the AMV precursor was heated inside the microscope and the electron diffraction patterns (DPs) of the phase transition were recorded and are presented in Figure 4e–g. Figure 4e shows the blurred DP without any sharp rings at room temperature corresponding to the amorphous AMV precursor. At 500 °C, the phase transition occurred from amorphous AMV precursor to crystalline V_2O_5 , which is evident from the bright rings in the DP in Figure 4f. Further increasing the temperature to 700 °C leads to the structural transition from orthorhombic V_2O_5 to rutile VO_2 , and the corresponding bright rings in the DP are evident of this

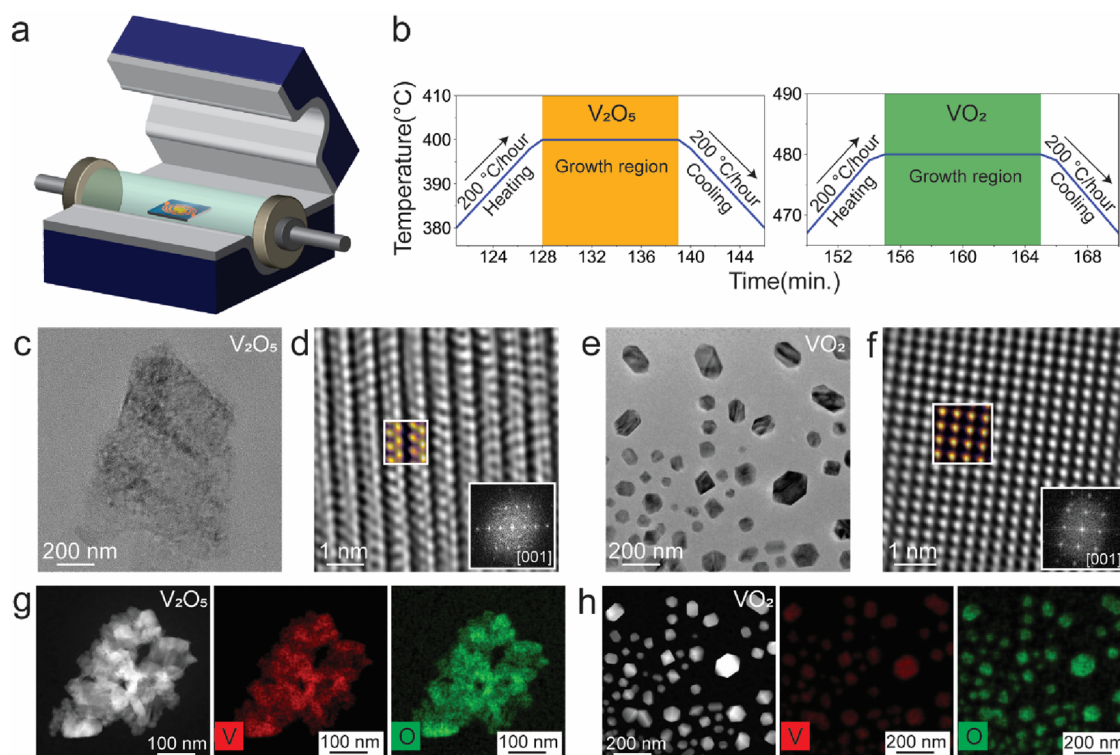


Figure 5. *Ex situ* growth of vanadium oxide structures. (a) Schematic representation of the setup for the *ex situ* experiment. (b) Temperature profiles for both V₂O₅ and VO₂ structures. (c) The TEM image of a thin V₂O₅ nanosheet. (d) The high-resolution image of orthorhombic V₂O₅ with an overlapped colored simulated image in a box, and the FFT in the inset. (e) The TEM image of VO₂ nanostructures. (f) The high-resolution TEM image of rutile VO₂ with an overlapped colored simulated image in a box, and FFT in the inset. (g, h) HAADF-STEM images of V₂O₅ and VO₂ structures in the first panels and EDS elemental maps for vanadium and oxygen in red and green colors, respectively.

transition. The details on the DPs with indexing of the bright rings to the corresponding planes in the V₂O₅ and VO₂ are shown in Supporting Figure S4.

Ex Situ Growth of V₂O₅ and VO₂ Nanostructures. An *in situ* TEM experiment provides important information on optimization and control of the growth of materials along with insights into the evolution of the growth. To scale up the synthesis or fabrication of the materials, it is necessary to grow materials in regular laboratory conditions. Hence, to support the *in situ* findings in thermolysis-driven growth of vanadium oxide nanostructures, *ex situ* experiments were carried out in the vacuum oven as depicted in the schematic in Figure 5a. The heating chips drop cast with AMV precursor were kept in the central part of the vacuum oven after setting it for the temperature controls. Here, in the *ex situ* experiments, the same heating chips are used to keep the same substrate interaction with the precursor and to observe the grown structures directly in the microscope without carrying any distinct sample preparation method. This gave a feasible opportunity to observe the as-grown structures without any possible disturbance from the electron beam. The temperature profiles during the growth for both V₂O₅ and VO₂ are shown in Figure 5b. In both cases, the heating and cooling rates were kept the same at 200 °C/h, and the temperature platforms of 400 and 480 °C for the growth of V₂O₅ and VO₂ were kept for time periods of 10 and 12 min, respectively. The growth temperatures for both V₂O₅ and VO₂ were optimized by carrying out several pilot experiments. One of the examples of the *ex situ* grown thin nanosheets of V₂O₅ is shown in Figure 5c, and the high-resolution image with the colored simulated image in the indicated box, along with the FFT pattern, is shown in Figure 5d.

The typical arrangements of atomic columns in the orthorhombic V₂O₅ are visible in the experimental high-resolution image and in the simulated image under the same conditions as that of the *in situ* experiment. The same sample transforms to the VO₂ after being heated to 480 °C, and the nanostructures of VO₂ are shown in Figure 5e along with the high-resolution image from one of the nanostructures in Figure 5f, with a colored simulated image in the indicated box, and the FFT pattern in the inset. HAADF-STEM images show the thinness of the V₂O₅ NSs in Figure 5g along with the elemental maps for V and O in red and green colors, respectively. The thin nanosheets of V₂O₅ transformed into the thick nanoparticles of VO₂, which is evident from the HAADF-STEM image in Figure 5h, where the shape of the particles is seen to be different from that of the thin nanosheets. The EDS elemental maps for V and O are represented in red and green, respectively, and the quantification of the EDS information shows a stoichiometry of 1:2 in VO₂. Thus, overall, the *ex situ* experiments performed in the vacuum oven produced similar structures of V₂O₅ and VO₂ nanostructures at slightly different temperatures compared to those in the *in situ* TEM experiments. The pressure difference between the TEM column and vacuum oven can be a major factor causing the transformation or other thermodynamic processes to take place at quite different temperatures. Also, in the current case, the pressure difference in the TEM column and vacuum oven plays a role, and hence, the phase transformation of V₂O₅ to VO₂ occurred at 480 °C in the *ex situ* experiment. Another aspect is the local nature of the heating inside the *in situ* TEM heating setup vs the broad *ex situ* heating inside the vacuum oven, which might also have played a role resulting in

differences in the observed temperatures for phase transformations.

CONCLUSIONS

In summary, we observed thermolysis-driven growth of V_2O_5 nanostructures on SiN_x membrane using a single solid-state precursor in combination with *in situ* TEM heating. Intermediate stages during the thermolysis of AMV precursor are observed in real time, which would be unreachable when using conventional methods. The growth temperatures required in the thermolysis of the AMV precursor to produce fully grown V_2O_5 nanostructures are optimized. The phase transformations from V_2O_5 to VO_2 are also observed in the *in situ* TEM experiments at elevated temperatures. Furthermore, the *ex situ* thermolysis of AMV precursor in a vacuum oven produced pure crystalline V_2O_5 and VO_2 nanostructures on the bare SiN_x membrane of the heating chip, which validates the thermolysis-driven growth as observed by means of *in situ* TEM. Controlling the thickness of the precursor and hence the thickness of grown 2D V_2O_5 nanostructures, along with the optimization of the parameters to control the morphology of V_2O_5 nanostructures, are still open challenges of this method. Our study offers a relatively simple method to produce pure crystalline V_2O_5 1D nanobelts and 2D nanosheets along with VO_2 nanostructures in a single-synthesis method that can be scaled up to produce desired materials for rechargeable batteries and catalytic applications.

ASSOCIATED CONTENT

Supporting Information

The Supporting Information is available free of charge at <https://pubs.acs.org/doi/10.1021/acsanm.3c00397>.

Additional figures show a schematic illustrating the drop-casting of ATT onto the heating chip and examination using the electron beam after the introduction of it in the TEM column for conducting the *in situ* TEM experiment, *in situ* heating temperature profiles of experiments describing the observed growth of different structures at particular temperature ranges, TEM images of the AMV precursor kept under the electron beam for more than 10 min at room temperature before and after the exposure, electron diffraction patterns (DP) during the *in situ* TEM heating experiment for the amorphous precursor, and orthorhombic V_2O_5 , and rutile phase VO_2 structures (PDF)

Growth of the V_2O_5 layer at 450 °C (slowed down to 1/2 times of real time) (Supporting Movie 1) (AVI)

AUTHOR INFORMATION

Corresponding Author

Marijn A. van Huis – *Soft Condensed Matter and Biophysics, Debye Institute for Nanomaterials Science, Utrecht University, Utrecht 3584 CC, The Netherlands*; orcid.org/0000-0002-8039-2256; Email: m.a.vanhuis@uu.nl

Authors

Dnyaneshwar S. Gavhane – *Soft Condensed Matter and Biophysics, Debye Institute for Nanomaterials Science, Utrecht University, Utrecht 3584 CC, The Netherlands*; orcid.org/0000-0002-9004-7624

Atul D. Sontakke – *Condensed Matter and Interfaces, Debye Institute for Nanomaterials Science, Utrecht University,*

Utrecht 3584 CC, The Netherlands; orcid.org/0000-0001-5132-0942

Complete contact information is available at: <https://pubs.acs.org/doi/10.1021/acsanm.3c00397>

Notes

The authors declare no competing financial interest.

ACKNOWLEDGMENTS

This project was financially supported by the European Research Council through an ERC Consolidator Grant NANO-INSITU (No. 683076). The authors thank Hans Meeldijk and Chris Schneijdenberg from Electron Microscopy Utrecht for help with TEM experimentation. We thank Prof. Dr. Alfons van Blaaderen for useful discussions on the project.

REFERENCES

- (1) Andrews, J. L.; Mukherjee, A.; Yoo, H. D.; Parija, A.; Marley, P. M.; Fakra, S.; Prendergast, D.; Cabana, J.; Klie, R. F.; Banerjee, S. Reversible Mg-ion insertion in a metastable one-dimensional polymorph of V_2O_5 . *Chem* **2018**, *4*, 564–585.
- (2) Gu, S.; Wang, H.; Wu, C.; Bai, Y.; Li, H.; Wu, F. Confirming reversible Al^{3+} storage mechanism through intercalation of Al^{3+} into V_2O_5 nanowires in a rechargeable aluminum battery. *Energy Storage Mater.* **2017**, *6*, 9–17.
- (3) Kundu, D.; Adams, B. D.; Duffort, V.; Vajargah, S. H.; Nazar, L. F. A high-capacity and long-life aqueous rechargeable zinc battery using a metal oxide intercalation cathode. *Nat. Energy* **2016**, *1*, 16119.
- (4) Xu, X.; Duan, M.; Yue, Y.; Li, Q.; Zhang, X.; Wu, L.; Wu, P.; Song, B.; Mai, L. Bilayered $Mg_{0.25}V_2O_5 \cdot H_2O$ as a stable cathode for rechargeable Ca-ion batteries. *ACS Energy Lett.* **2019**, *4*, 1328–1335.
- (5) Zhu, Y.-H.; Zhang, Q.; Yang, X.; Zhao, E.-Y.; Sun, T.; Zhang, X.-B.; Wang, S.; Yu, X.-Q.; Yan, J.-M.; Jiang, Q. Reconstructed orthorhombic V_2O_5 polyhedra for fast ion diffusion in K-ion batteries. *Chem* **2019**, *5*, 168–179.
- (6) Wang, C.; Zhang, L.; Al-Mamun, M.; Dou, Y.; Liu, P.; Su, D.; Wang, G.; Zhang, S.; Wang, D.; Zhao, H. A Hollow-Shell Structured V_2O_5 Electrode-Based Symmetric Full Li-Ion Battery with Highest Capacity. *Adv. Energy Mater.* **2019**, *9*, 1900909.
- (7) Wang, J.; Tang, H.; Zhang, L.; Ren, H.; Yu, R.; Jin, Q.; Qi, J.; Mao, D.; Yang, M.; Wang, Y.; Liu, P.; Zhang, Y.; Wen, Y.; Gu, L.; Ma, G.; Su, Z.; Tang, Z.; Zhao, H.; Wang, D. Multi-shelled metal oxides prepared via an anion-adsorption mechanism for lithium-ion batteries. *Nat. Energy* **2016**, *1*, 16050.
- (8) Zhu, Y.; Yang, M.; Huang, Q.; Wang, D.; Yu, R.; Wang, J.; Zheng, Z.; Wang, D. V_2O_5 textile cathodes with high capacity and stability for flexible lithium-ion batteries. *Adv. Mater.* **2020**, *32*, 1906205.
- (9) Li, B.; Xu, Y.; Rong, G.; Jing, M.; Xie, Y. Vanadium pentoxide nanobelts and nanorolls: from controllable synthesis to investigation of their electrochemical properties and photocatalytic activities. *Nanotechnology* **2006**, *17*, 2560.
- (10) Alrammouz, R.; Lazerges, M.; Pironon, J.; Taher, I. B.; Randi, A.; Halfaya, Y.; Gautier, S. V_2O_5 gas sensors: A review. *Sens. Actuators, A* **2021**, *332*, No. 113179.
- (11) Liu, J.; Wang, X.; Peng, Q.; Li, Y. Preparation and gas sensing properties of vanadium oxide nanobelts coated with semiconductor oxides. *Sens. Actuators, B* **2006**, *115*, 481–487.
- (12) Schneider, K.; Lubecka, M.; Czapla, A. V_2O_5 thin films for gas sensor applications. *Sens. Actuators, B* **2016**, *236*, 970–977.
- (13) Liu, X.; Zeng, J.; Yang, H.; Zhou, K.; Pan, D. V_2O_5 -based nanomaterials: synthesis and their applications. *RSC Adv.* **2018**, *8*, 4014–4031.
- (14) Glushenkov, A. M.; Stukachev, V. I.; Hassan, M. F.; Kuvshinov, G. G.; Liu, H. K.; Chen, Y. A novel approach for real mass transformation from V_2O_5 particles to nanorods. *Cryst. Growth Des.* **2008**, *8*, 3661–3665.

- (15) Glushenkov, A. M.; Hassan, M. F.; Stukachev, V. I.; Guo, Z.; Liu, H. K.; Kuvshinov, G. G.; Chen, Y. Growth of V_2O_5 nanorods from ball-milled powders and their performance in cathodes and anodes of lithium-ion batteries. *J. Solid State Electrochem.* **2010**, *14*, 1841–1846.
- (16) Rui, X.; Tang, Y.; Malyi, O. I.; Gusak, A.; Zhang, Y.; Niu, Z.; Tan, H. T.; Persson, C.; Chen, X.; Chen, Z.; Yan, Q. Ambient dissolution–recrystallization towards large-scale preparation of V_2O_5 nanobelts for high-energy battery applications. *Nano Energy* **2016**, *22*, 583–593.
- (17) Qin, M.; Liang, Q.; Pan, A.; Liang, S.; Zhang, Q.; Tang, Y.; Tan, X. Template-free synthesis of vanadium oxides nanobelt arrays as high-rate cathode materials for lithium ion batteries. *J. Power Sources* **2014**, *268*, 700–705.
- (18) Cheah, Y. L.; Gupta, N.; Pramana, S. S.; Aravindan, V.; Wee, G.; Srinivasan, M. Morphology, structure and electrochemical properties of single phase electrospun vanadium pentoxide nanofibers for lithium ion batteries. *J. Power Sources* **2011**, *196*, 6465–6472.
- (19) An, Q.; Wei, Q.; Mai, L.; Fei, J.; Xu, X.; Zhao, Y.; Yan, M.; Zhang, P.; Huang, S. Supercritically exfoliated ultrathin vanadium pentoxide nanosheets with high rate capability for lithium batteries. *Phys. Chem. Chem. Phys.* **2013**, *15*, 16828–16833.
- (20) Rui, X.; Lu, Z.; Yu, H.; Yang, D.; Hng, H. H.; Lim, T. M.; Yan, Q. Ultrathin V_2O_5 nanosheet cathodes: realizing ultrafast reversible lithium storage. *Nanoscale* **2013**, *5*, 556–560.
- (21) Wang, C.; Yi, Y.; Li, H.; Wu, P.; Li, M.; Jiang, W.; Chen, Z.; Li, H.; Zhu, W.; Dai, S. Rapid gas-assisted exfoliation promises V_2O_5 nanosheets for high performance lithium-sulfur batteries. *Nano Energy* **2020**, *67*, No. 104253.
- (22) Xu, Y.; Dunwell, M.; Fei, L.; Fu, E.; Lin, Q.; Patterson, B.; Yuan, B.; Deng, S.; Andersen, P.; Luo, H.; Zou, G. Two-dimensional V_2O_5 sheet network as electrode for lithium-ion batteries. *ACS Appl. Mater. Interfaces* **2014**, *6*, 20408–20413.
- (23) Li, Y.; Yao, J.; Uchaker, E.; Yang, J.; Huang, Y.; Zhang, M.; Cao, G. Leaf-Like V_2O_5 Nanosheets Fabricated by a Facile Green Approach as High Energy Cathode Material for Lithium-Ion Batteries. *Adv. Energy Mater.* **2013**, *3*, 1171–1175.
- (24) Chen, M.; Xia, X.; Yuan, J.; Yin, J.; Chen, Q. Free-standing three-dimensional continuous multilayer V_2O_5 hollow sphere arrays as high-performance cathode for lithium batteries. *J. Power Sources* **2015**, *288*, 145–149.
- (25) Feng, C. Q.; Wang, S. Y.; Zeng, R.; Guo, Z. P.; Konstantinov, K.; Liu, H. K. Synthesis of spherical porous vanadium pentoxide and its electrochemical properties. *J. Power Sources* **2008**, *184*, 485–488.
- (26) Dong, Y.; Wei, H.; Liu, W.; Liu, Q.; Zhang, W.; Yang, Y. Template-free synthesis of V_2O_5 hierarchical nanosheet-assembled microspheres with excellent cycling stability. *J. Power Sources* **2015**, *285*, 538–542.
- (27) Pan, A.; Wu, H. B.; Yu, L.; Zhu, T.; Lou, X. W. Synthesis of hierarchical three-dimensional vanadium oxide microstructures as high-capacity cathode materials for lithium-ion batteries. *ACS Appl. Mater. Interfaces* **2012**, *4*, 3874–3879.
- (28) Song, H.; Zhang, C.; Liu, Y.; Liu, C.; Nan, X.; Cao, G. Facile synthesis of mesoporous V_2O_5 nanosheets with superior rate capability and excellent cycling stability for lithium ion batteries. *J. Power Sources* **2015**, *294*, 1–7.
- (29) Biedunkiewicz, A.; Gabriel, U.; Figiel, P.; Sabara, M. Investigations on NH_4VO_3 thermal decomposition in dry air. *J. Therm. Anal. Calorim.* **2012**, *108*, 965–970.
- (30) Brock, L. R.; Keister, J. W.; France, M.; Fierro, N.; DeVore, T. C. The thermal decomposition of ammonium meta-vanadate under restricted flow conditions. *Am. J. Anal. Chem.* **2017**, *08*, 35–50.
- (31) Khulbe, K. C.; Mann, R. S. Thermal Decomposition of Ammonium Metavanadate. *Can. J. Chem.* **1975**, *53*, 2917–2921.
- (32) Range, K.-J.; Zintl, R.; Heyns, A. M. The thermal decomposition of ammonium metavanadate (V) in open and closed systems. *Z. Naturforsch., B* **1988**, *43*, 309–317.
- (33) Cora, I.; Fogarassy, Z.; Fornari, R.; Bosi, M.; Rečnik, A.; Pécz, B. In situ TEM study of $\kappa \rightarrow \beta$ and $\kappa \rightarrow \gamma$ phase transformations in Ga_2O_3 . *Acta Mater.* **2020**, *183*, 216–227.
- (34) Gavhane, D. S.; van Gog, H.; Thombare, B.; Lole, G.; Christiaan Post, L.; More, M. A.; van Huis, M. A. In situ electron microscopy study of structural transformations in 2D $CoSe_2$. *npj 2D Mater. Appl.* **2021**, *5*, 24.
- (35) Singh, M.; Ghosh, C.; Kotula, P.; Watt, J.; Silva, H.; Carter, C. B. Direct Observation of Phase Transformations in Ge-Sb-Te Materials. *Microsc. Microanal.* **2020**, *26*, 1418–1420.
- (36) van Huis, M. A.; Young, N. P.; Pandraud, G.; Creemer, J. F.; Vanmaekelbergh, D.; Kirkland, A. I.; Zandbergen, H. W. Atomic imaging of phase transitions and morphology transformations in nanocrystals. *Adv. Mater.* **2009**, *21*, 4992–4995.
- (37) Lin, T.-Y.; Chen, Y.-L.; Chang, C.-F.; Huang, G.-M.; Huang, C.-W.; Hsieh, C.-Y.; Lo, Y.-C.; Lu, K.-C.; Wu, W.-W.; Chen, L.-J. In situ investigation of defect-free copper nanowire growth. *Nano Lett.* **2018**, *18*, 778–784.
- (38) Maliakkal, C. B.; Jacobsson, D.; Tornberg, M.; Persson, A. R.; Johansson, J.; Wallenberg, R.; Dick, K. A. In situ analysis of catalyst composition during gold catalyzed GaAs nanowire growth. *Nat. Commun.* **2019**, *10*, 1–9.
- (39) Sun, Q.; Pan, D.; Li, M.; Zhao, J.; Chen, P.; Lu, W.; Zou, J. In situ TEM observation of the vapor–solid–solid growth of $\langle 00-1 \rangle$ InAs nanowires. *Nanoscale* **2020**, *12*, 11711–11717.
- (40) Buha, J.; Gaspari, R.; Del Rio Castillo, A. E.; Bonaccorso, F.; Manna, L. Thermal stability and anisotropic sublimation of two-dimensional colloidal Bi_2Te_3 and Bi_2Se_3 nanocrystals. *Nano Lett.* **2016**, *16*, 4217–4223.
- (41) Li, J.; Wang, Z.; Li, Y.; Deepak, F. L. In situ atomic-scale observation of kinetic pathways of sublimation in silver nanoparticles. *Adv. Sci.* **2019**, *6*, 1802131.
- (42) Luo, C.; Li, J.; Yang, X.; Wu, X.; Zhong, S.; Wang, C.; Sun, L. In situ interfacial sublimation of Zn_2GeO_4 nanowire for atomic-scale manufacturing. *ACS Appl. Nano Mater.* **2020**, *3*, 4747–4754.
- (43) Chen, J.; Ryu, G. H.; Sinha, S.; Warner, J. H. Atomic structure and dynamics of defects and grain boundaries in 2D Pd_2Se_3 monolayers. *ACS Nano* **2019**, *13*, 8256–8264.
- (44) Mendes, R. G.; Pang, J.; Bachmatiuk, A.; Ta, H. Q.; Zhao, L.; Gemming, T.; Fu, L.; Liu, Z.; Rummeli, M. H. Electron-driven in situ transmission electron microscopy of 2D transition metal dichalcogenides and their 2D heterostructures. *ACS Nano* **2019**, *13*, 978–995.
- (45) Ryu, G. H.; Chen, J.; Wen, Y.; Warner, J. H. In-situ atomic-scale dynamics of thermally driven phase transition of 2D few-layered 1T $PtSe_2$ into ultrathin 2D nonlayered $PtSe$ crystals. *Chem. Mater.* **2019**, *31*, 9895–9903.
- (46) Ryu, G. H.; France-Lanord, A.; Wen, Y.; Zhou, S.; Grossman, J. C.; Warner, J. H. Atomic structure and dynamics of self-limiting subnanometer pores in monolayer WS_2 . *ACS Nano* **2018**, *12*, 11638–11647.
- (47) Sang, X.; Li, X.; Zhao, W.; Dong, J.; Rouleau, C. M.; Geoghegan, D. B.; Ding, F.; Xiao, K.; Unocic, R. R. In situ edge engineering in two-dimensional transition metal dichalcogenides. *Nat. Commun.* **2018**, *9*, 2051.
- (48) Tai, K. L.; Huang, C. W.; Cai, R. F.; Huang, G. M.; Tseng, Y. T.; Chen, J.; Wu, W. W. Atomic-scale fabrication of in-plane heterojunctions of few-layer MoS_2 via in situ scanning transmission electron microscopy. *Small* **2020**, *16*, 1905516.
- (49) Sutter, E.; Huang, Y.; Komsa, H.-P.; Ghorbani-Asl, M.; Krasheninnikov, A. V.; Sutter, P. Electron-beam induced transformations of layered tin dichalcogenides. *Nano Lett.* **2016**, *16*, 4410–4416.
- (50) Fei, L.; Lei, S.; Zhang, W.-B.; Lu, W.; Lin, Z.; Lam, C. H.; Chai, Y.; Wang, Y. Direct TEM observations of growth mechanisms of two-dimensional MoS_2 flakes. *Nat. Commun.* **2016**, *7*, 12206.
- (51) Sang, X.; Li, X.; Puzetzy, A. A.; Geoghegan, D. B.; Xiao, K.; Unocic, R. R. Atomic insight into thermolysis-driven growth of 2D MoS_2 . *Adv. Funct. Mater.* **2019**, *29*, 1902149.
- (52) Kondekar, N.; Boebinger, M. G.; Tian, M.; Kirmani, M. H.; McDowell, M. T. The effect of nickel on MoS_2 growth revealed with in situ transmission electron microscopy. *ACS Nano* **2019**, *13*, 7117–7126.

(53) Zhang, Y.; Zhang, Z.; Cheng, Y.; Cheng, F.; Wang, L.; Liu, N.; Li, L.; Su, J.; Gao, Y. In situ TEM observation of controlled growth of two-dimensional WS₂ with vertically aligned layers and high-temperature stability. *Nano Energy* **2020**, *67*, No. 104221.

(54) Gavhane, D. S.; Sontakke, A. D.; Huis, M. A. Selective Vertical and Horizontal Growth of 2D WS₂ Revealed by In Situ Thermolysis using Transmission Electron Microscopy. *Adv. Funct. Mater.* **2022**, *32*, 2106450.

(55) Chen, C. L.; Mori, H. In situ TEM observation of the growth and decomposition of monoclinic W₁₈O₄₉ nanowires. *Nanotechnology* **2009**, *20*, No. 285604.

(56) Li, X.; Cheng, S.; Deng, S.; Wei, X.; Zhu, J.; Chen, Q. Direct observation of the layer-by-layer growth of ZnO nanopillar by in situ high resolution transmission electron microscopy. *Sci. Rep.* **2017**, *7*, 40911.

(57) Chang, J.-H.; Tseng, Y.-T.; Ho, A.-Y.; Lo, H.-Y.; Huang, C.-Y.; Tsai, S.-C.; Yu, T.-H.; Wu, Y.-L.; Yen, H.-K.; Yeh, P.-H.; Lu, K. C.; Wu, W. W. In situ TEM investigation of indium oxide/titanium oxide nanowire heterostructures growth through solid state reactions. *Mater. Charact.* **2022**, *187*, No. 111832.

(58) Hussein, H. E. M.; Beanland, R.; Sánchez, A. M.; Walker, D.; Walker, M.; Han, Y.; Macpherson, J. V. Atomic-scale investigation of the reversible α -to ω -phase lithium ion charge–discharge characteristics of electrodeposited vanadium pentoxide nanobelts. *J. Mater. Chem. A* **2022**, *10*, 8515–8527.

(59) Niu, C.; Li, J.; Jin, H.; Shi, H.; Zhu, Y.; Wang, W.; Cao, M. Self-template processed hierarchical V₂O₅ nanobelts as cathode for high performance lithium ion battery. *Electrochim. Acta* **2015**, *182*, 621–628.

(60) Huang, J.; Qiao, X.; Xu, Z.; Cao, L.; Ouyang, H.; Li, J.; Wang, R. V₂O₅ self-assembled nanosheets as high stable cathodes for Lithium-ion batteries. *Electrochim. Acta* **2016**, *191*, 158–164.

(61) Wu, H.; Qin, M.; Li, X.; Cao, Z.; Jia, B.; Zhang, Z.; Zhang, D.; Qu, X.; Volinsky, A. A. One step synthesis of vanadium pentoxide sheets as cathodes for lithium ion batteries. *Electrochim. Acta* **2016**, *206*, 301–306.

(62) Wang, P.-P.; Yao, Y.-X.; Xu, C.-Y.; Wang, L.; He, W.; Zhen, L. Self-standing flexible cathode of V₂O₅ nanobelts with high cycling stability for lithium-ion batteries. *Ceram. Int.* **2016**, *42*, 14595–14600.

(63) Liang, S.; Hu, Y.; Nie, Z.; Huang, H.; Chen, T.; Pan, A.; Cao, G. Template-free synthesis of ultra-large V₂O₅ nanosheets with exceptional small thickness for high-performance lithium-ion batteries. *Nano Energy* **2015**, *13*, 58–66.

(64) Lu, Q.; Bishop, S. R.; Lee, D.; Lee, S.; Bluhm, H.; Tuller, H. L.; Lee, H. N.; Yildiz, B. Electrochemically triggered metal–insulator transition between VO₂ and V₂O₅. *Adv. Funct. Mater.* **2018**, *28*, 1803024.

(65) Pei, G.; Xiang, J.; Zhong, D.; Li, G.; Lv, X. Isothermal reduction of V₂O₅ powder using H₂ as oxygen carrier: Thermodynamic evaluation, reaction sequence, and kinetic analysis. *Powder Technol.* **2021**, *378*, 785–794.

(66) Zhang, C.; Koughia, C.; Gunes, O.; Li, X.; Li, Y.; Feng, R.; Wen, S.; Wong, R.; Yang, Q.; Kasap, S. Size, composition and alignment of VO₂ microrod crystals by the reduction of V₂O₅ thin films, and their optical properties through insulator-metal transitions. *J. Alloys Compd.* **2020**, *827*, No. 154150.

(67) Zhang, C.; Koughia, C.; Zhu, J.; Feng, R.; Gunes, O.; Wen, S.; Yang, Q.; Kasap, S. Self-assembled single crystal VO₂ (A) microbelts by the reduction of V₂O₅ thin films: synthesis, structure and optical properties. *J. Alloys Compd.* **2021**, *863*, No. 158728.

(68) He, X.; Xu, T.; Xu, X.; Zeng, Y.; Xu, J.; Sun, L.; Wang, C.; Xing, H.; Wu, B.; Lu, A.; Liu, D.; Chen, X.; Chu, J. In situ atom scale visualization of domain wall dynamics in VO₂ insulator-metal phase transition. *Sci. Rep.* **2014**, *4*, 6544.

(69) Morin, F. J. Oxides which show a metal-to-insulator transition at the Neel temperature. *Phys. Rev. Lett.* **1959**, *3*, 34.

(70) Sun, G.; Cao, X.; Gao, X.; Long, S.; Liang, M.; Jin, P. Structure and enhanced thermochromic performance of low-temperature fabricated VO₂/V₂O₃ thin film. *Appl. Phys. Lett.* **2016**, *109*, 143903.

Recommended by ACS

Revealing Controlled Etching Behaviors of Gold Nanobipyramids by Carbon Film Liquid Cell Transmission Electron Microscopy

Wei Wei, Zhirui Guo, *et al.*

APRIL 18, 2023

THE JOURNAL OF PHYSICAL CHEMISTRY C

READ 

Tungsten Oxide Mediated Quasi-van der Waals Epitaxy of WS₂ on Sapphire

Assael Cohen, Ariel Ismach, *et al.*

MARCH 08, 2023

ACS NANO

READ 

1D Germanium Sulfide van der Waals Bicrystals by Vapor–Liquid–Solid Growth

Eli Sutter, Peter Sutter, *et al.*

FEBRUARY 11, 2022

ACS NANO

READ 

Regulated Dynamics with Two Monolayer Steps in Vapor–Solid–Solid Growth of Nanowires

Edith Bellet-Amalric, Joël Cibert, *et al.*

MARCH 11, 2022

ACS NANO

READ 

Get More Suggestions >